

Original citation:

Iqbal, Parvez, Mayanditheuar, Manickam, Childs, Laura J., Hannon, Michael J., Spencer, Neil, Ashton, Peter R. and Preece, Jon A.. (2009) Preparation of novel banana-shaped triple helical liquid crystals by metal coordination. *Materials*, Volume 2 (Number 1). pp. 146-168.

Permanent WRAP url:

<http://wrap.warwick.ac.uk/60525>

Copyright and reuse:

The Warwick Research Archive Portal (WRAP) makes this work of researchers of the University of Warwick available open access under the following conditions.

This article is made available under the Creative Commons Attribution- 3.0 Unported (CC BY 3.0) license and may be reused according to the conditions of the license. For more details see <http://creativecommons.org/licenses/by/3.0/>

A note on versions:

The version presented in WRAP is the published version, or, version of record, and may be cited as it appears here.

For more information, please contact the WRAP Team at: publications@warwick.ac.uk

Article

Preparation of Novel Banana-Shaped Triple Helical Liquid Crystals by Metal Coordination

Parvez Iqbal ¹, Manickam Mayanditheuar ^{1,*}, Laura J. Childs ², Michael J. Hannon ^{1,2}, Neil Spencer ¹, Peter R. Ashton ¹ and Jon A. Preece ¹

¹ School of Chemistry, The University of Birmingham, Birmingham, Edgbaston, United Kingdom, B15 2TT; E-Mails: p.iqbal@bham.ac.uk (P.I.); m.j.hannon@bham.ac.uk (M.H.);

n.spencer@bham.ac.uk (N.S.); p.r.ashton@bham.ac.uk (P.A.); j.a.preece@bham.ac.uk (J.P.)

² Department of Chemistry, University of Warwick, Coventry, United Kingdom, CV4 7AL; E-Mail: laurachilds10@yahoo.co.uk

* Author to whom correspondence should be addressed; E-Mail: M.Manickam@bham.ac.uk; Tel. +44 (0) 121 414 8908; Fax: +44 (0) 121 414 4403

Received: 2 February 2009; in revised form: 25 February 2009 / Accepted: 11 March 2009 /

Published: 13 March 2009

Abstract: The synthesis of a series of banana-shaped structures has been carried out, in which the bend unit is formed by a 4,4'-methylenedianiline or 3,3'-methylenedianiline core bearing two symmetric pyridylimine linkages to di- and tri- alkoxyphenylester moieties on the side arms. The molecules, in addition to providing an elongated aromatic central core associated with liquid crystal (LC) molecules, also provide binding sites for metals. The methylenedianiline spacer incorporates phenylene groups that sterically prevent the two binding sites from co-ordinating to a single metal centre and the central methylene unit introduces enhanced flexibility into the ligand backbone. Furthermore, complexes have been formed by the co-ordination between 3, 3'-methylenedianiline containing ligands and Cu (I) ions $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$. Electrospray Mass Spectrometry (ESMS) and Fast Atom Bombardment Mass Spectrometry (FABMS) showed the formation of dimeric species; $[\text{Cu}(\text{L})_2][\text{PF}_6]_2$. Finally, thermal analysis of the ligands (**1a-d**, **2a-d**, **3a-c** and **4a-d**) and Cu complexes $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$ has been carried out in order to investigate the phase properties of these materials. None of the banana-shaped ligands and the metal complexes $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$ showed any mesophases.

Keywords: Metallomesogens; banana; liquid crystals; triple helical; mesogenic.

1. Introduction


Although classical thermotropic liquid crystals (LCs) are commonly composed of rod-like molecules, many liquid crystals exhibit unconventional molecular structures. An example of such a molecular architecture is a banana-shaped one, with a bend in the middle of the mesogenic part [1-4]. Niori *et al.* [5] first observed ferroelectricity in a smectic phase which was produced from achiral banana-shaped molecules. Since then, several other research groups have [6] reported banana-shaped molecules that exhibited ferroelectric properties in the mesophase. The ferroelectricity is attributed to the polar packing of molecules with C_{2v} symmetry where the molecules are packed in the same direction. A great many analogous banana-shaped structures have been prepared, some with lateral substituents in the central aromatic ring, which exhibit the wide range of 'banana phases' commonly designated B₁ through to B₇ [7]. The existence of such mesophases depends on the length of the rigid core, as well as on the magnitude of the bend angle and its position. The structure and flexibility of the angled segment are also important [8].

Dating back to the 1980s there has been immense interest in metal-containing mesogens, and subsequently a novel subfield in liquid crystals has emerged, known as metallomesogens. One of the factors contributing to this growth of interest has been due to the presence of the metal atom causing significant change in the magnetic, electric and optical properties of liquid crystals [9-11]. Many liquid crystals calamites based on rare earth element complexes [9] have exhibited enhance magnetic susceptibility among liquid crystals, for example Dy and Tb complexes with Schiff's bases and β -aminovinyl ketones demonstrate high anisotropies of magnetic susceptibility [9]. At present, the molecular motifs of the known metallomesogens are based on the classical rod-like [12-15] and disc-shaped mesogens [16]. One of the modern pioneers in this field is Bruce *et al.*, who has demonstrated [12-15] that by a suitable choice of anisotropic ligand, it is possible to form rod-like liquid crystals based on the metals with octahedral coordination geometry [12,13]. Strong chelating moieties such as 2,2'-bipyridine [12] and imine [13] moieties have been utilised as the metal chelating units in these metallomesogens. Also, Ziessel *et al.*, have prepared several ligands based on 2,2'-bipyridine and these ligands assembled into a dinuclear double-helicate complex with copper that exhibits columnar mesophase [17].

Hannon *et al.* [18,19] have shown that bispyridylimine ligands can form double or triple stranded helicate structures. The triple helicate arises through the entwining of three bispyridylimine ligand strands around two metal cations, while the double helicates arise with tetrahedral metal ions. Herein, two novel series of banana-shaped molecules have been prepared that incorporate metal binding units (Scheme 1). The binding units contain 4,4'-methylenedianiline and 3,3'-methylenedianiline moieties as the central units which are linked to pyridine-2-carbaldehyde, affording imine structures. It is envisaged from the chemistry of the unsubstituted analogues (X-ray structures of their complexes are known [18,19,20]) that the helicates formed from the 4,4'-methylenedianiline core will form gross linear structures [18,21] and hence chemical modification at the terminal of this helicate with alkyl chains will result in classical rod-like mesogenic structures. Whereas, the helicates formed from the

3,3'-methylenedianiline which is structurally constrained will develop a kink at the centre of the helicate [20] and thus, with alkyl chains at the terminal of the helicate will form novel banana mesogenic structures $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$. The thermal properties of these ligands (**1a-d**, **2a-d**, **3a-c** and **4a-d**) and complexes $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$ have been investigated.

Scheme 1. Desired banana-shaped molecules and the preparation of Cu complexes.

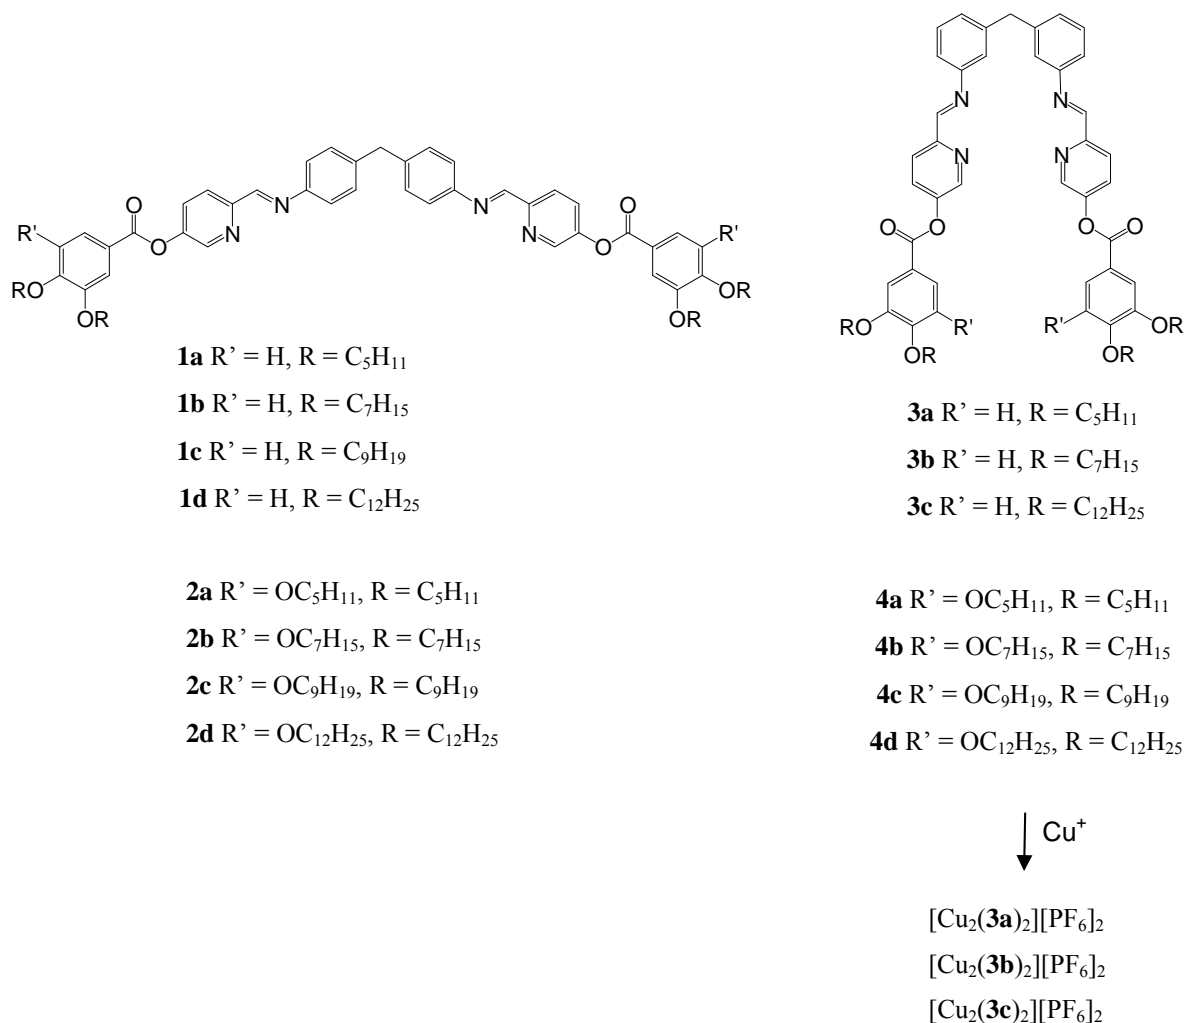

2. Results and Discussion

2.1. Design

The exact relationship between angled molecular structures and liquid crystalline properties is still not very clear to date, but empirical rules about molecular design [22-27] have shown that this new class of banana mesogen is extremely sensitive to structural modification regarding the attainment of mesophases. For example, flexibility [22,28], bend angle [7,28], nature of the central core [22,29-31], length [26,31] and nature [32] of the terminal chains, substituents both on the central [7,26], and on the side arms [33], dipoles [26], and direction of linking groups [34] are among the main variants contributing to the capability of a material to exhibit liquid crystalline properties.

Here a synthetic scheme has been devised that allows the incorporation of 4,4'-methylenedianiline and 3,3'-methylenedianiline units as the central core of the molecular architecture, which as well as providing the bent core for the banana-shaped molecules, provide pyridylimine and methylene dianiline units for binding to metal ions.

2.2. Synthesis

The syntheses of the novel banana-shaped compounds (**1a-d**, **2a-d**, **3a-c** and **4a-d**) were achieved via a series of reactions as illustrated in Scheme 2. The commercially available di- and trihydroxy benzoic acids **6** and **7** were converted to their respective methyl esters in the presence of a catalytic amount of concentrated H₂SO₄ in MeOH to afford compounds **8** and **9**. Alkylation of compounds **8** and **9** was achieved under basic conditions (K₂CO₃) with *n*-bromopentane, *n*-bromoheptane, *n*-bromononane and *n*-bromododecane, respectively affording compounds **10a-d** and **11a-d** [13]. The esters **10a-d** and **11a-d** were hydrolysed to the corresponding acids **12a-d** and **13a-d** under basic conditions (NaOH) [13]. The commercially available 5-hydroxy-2-methylpyridine (**14**) was directly oxidised with H₂O₂ to afford the N-oxide **15**. The N-oxide was subsequently heated in acetic anhydride to afford the acetate **16**. Under acidic conditions (concentrated HCl) compound **16** was deprotected to afford the alcohol **17**. Selective oxidation of the alcohol moiety was achieved in the presence of a mild oxidising agent, MnO₂ [35], to afford compound **18**. Compound **18** was then coupled with the acids **12a-d** and **13a-d** through dicyclohexylcarbodiimide (DCC) [13] coupling to afford the respective aldehydes **19a-d** and **20a-d**. The target imine compounds **1a-d**, **2a-d**, **3a-c** and **4a-d** were obtained via stirring under N₂ atmosphere at room temperature between the respective aldehydes **19a-d** and **20a-d** and methylene dianilines [36]. Finally, the complexes [Cu₂(**3a-c**)₂][PF₆]₂ were formed by coordination of molecules **3a-c** to Cu (I) ions at room temperature in *iso*-PrOH [18,21].

2.3. Thermal Properties of Bent-shaped Ligands

Thermal analysis was carried out on compounds **1a-d**, **2a-d**, **3a-c** and **4a-d** using variable temperature optical polarised microscope (OPM) between crossed polarisers, and differential scanning calorimetry (DSC). OPM revealed that upon heating from solid to the liquid phase, no birefringent liquids were formed, and the materials passed straight to the isotropic liquid phase. On cooling the I→K transition was observed at slightly lower temperatures, confirming the lack of any mesophase formation. However, for a few of the compounds (**2a**, **4c-d**) the I→K transition was not observed. This result suggests that these compounds decomposed through the K→I transition. As expected, for all the **1a-d**, **2a**, **2d**, **4c** and **4d** derivatives, the K→I transition decreased with increasing the length of the carbon chain. The DSC traces are illustrated in Figure 1 and the melting points are listed in Table 1.

Scheme 2. Synthesis of the desired banana-shaped molecules

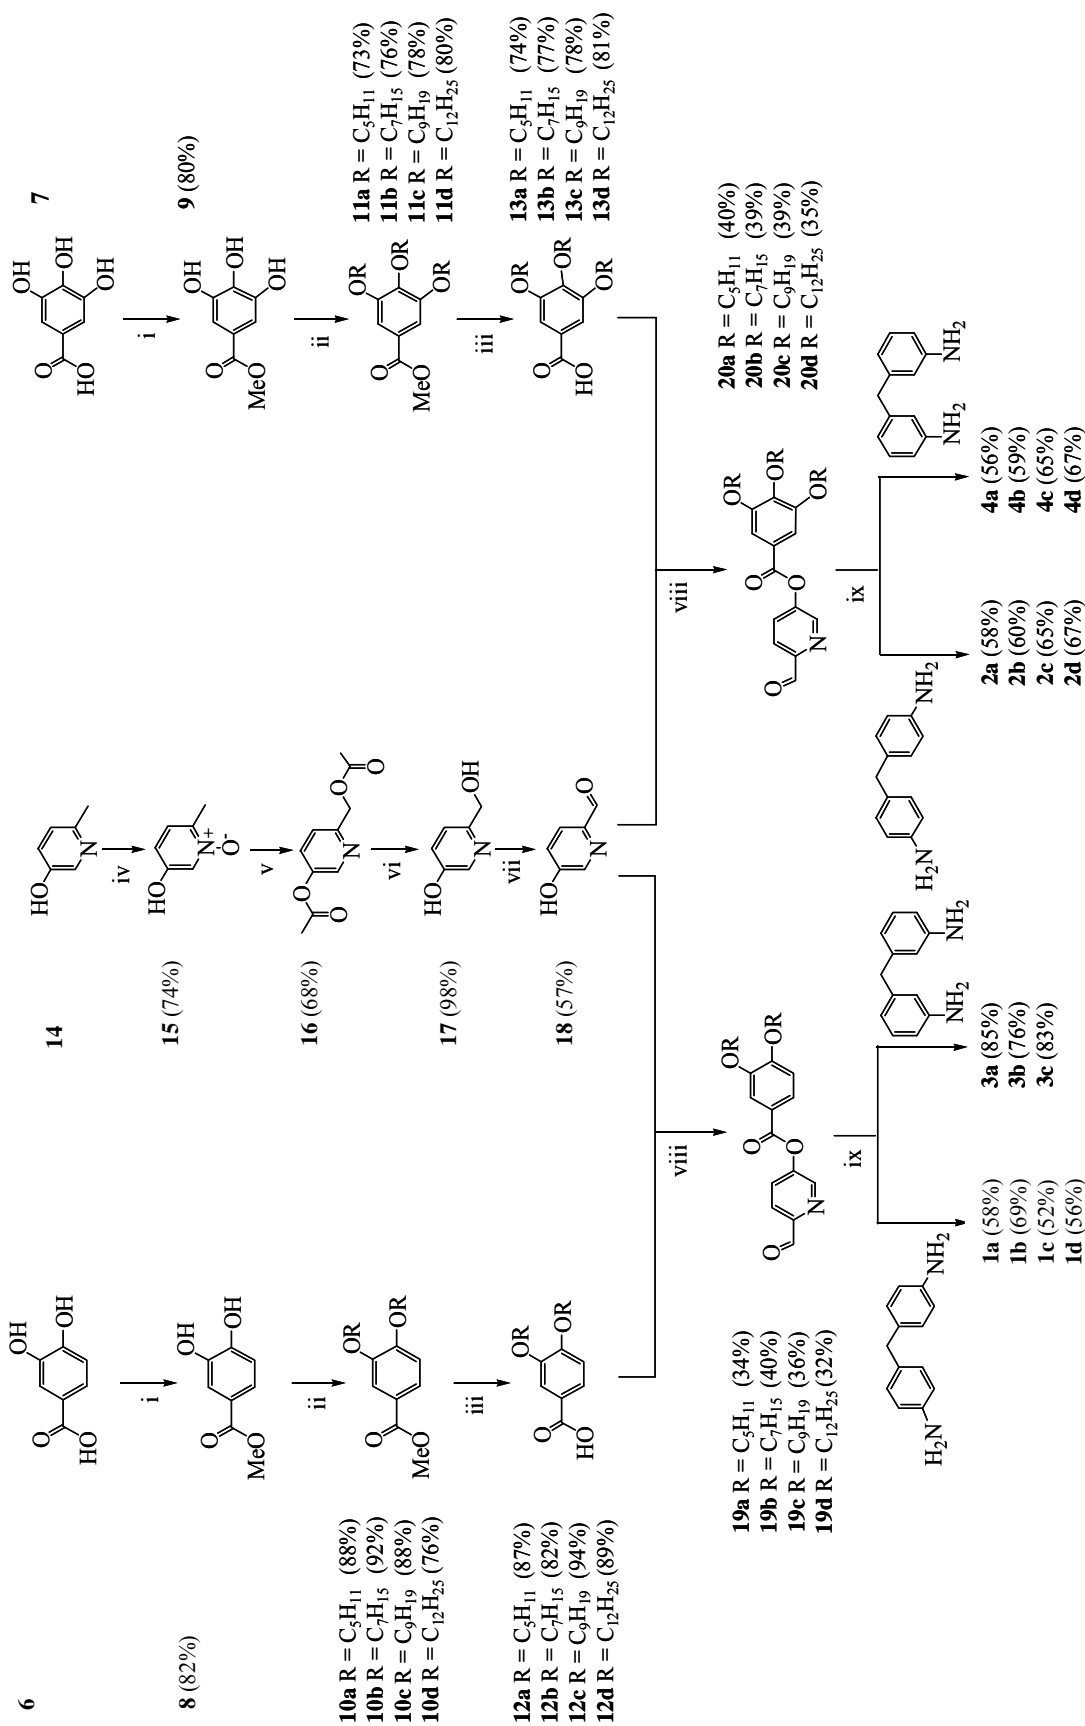


Figure 1. DSC traces for compounds **1a**, **1d**, **2a**, **2d**, **4c** and **4d** (second heating cycle at a rate of 5 °C/min).

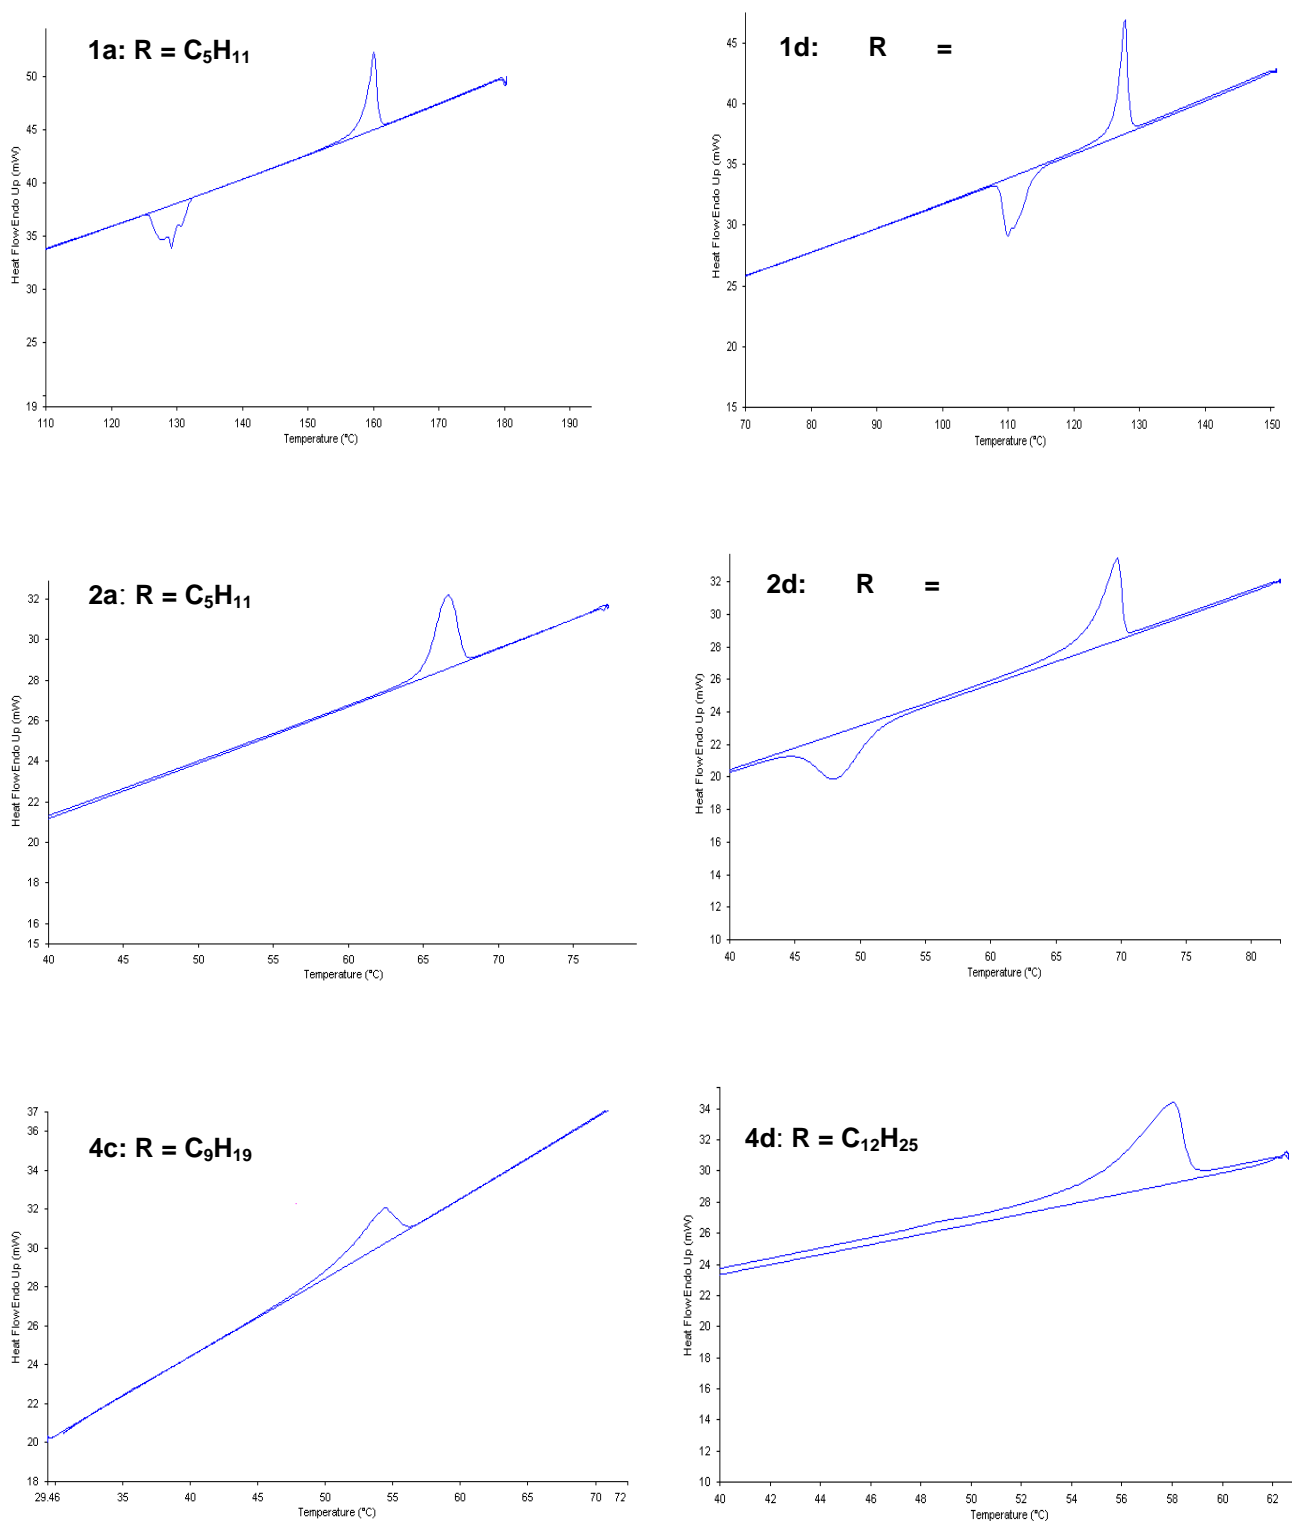


Table 1. Transition temperatures (onset values) (°C) and enthalpy values ΔH (kJ/mol) recorded on second heating by DSC (10 °C/min) for compounds **1a-d**, **2a**, **2d**, **4c** and **4d**.

Entry	K→I	ΔH
1a	158	81.3
1b	136	64.3
1c	129	40.0
1d	126	81.0
2a	67	43.7
2d	51	115.8
4c	51	60.8
4d	55	85.4

2.4. Metal Complexes

Cu complexes $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$ were isolated as red precipitates and through UV/vis spectroscopy λ_{max} are determined as 495, 485 and 480 nm, respectively, which are characteristic for Cu (I) ions in a bis-pyridylimine environment [18,20,21]. The masses obtained for complexes $[\text{Cu}_2(\mathbf{3a})_2][\text{PF}_6]_2$ and $[\text{Cu}_2(\mathbf{3b})_2][\text{PF}_6]_2$ from ES and FAB mass spectrometry, show that the species formed are dinuclear double stranded arrays in the form of $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$. In the case of $[\text{Cu}_2(\mathbf{3c})_2][\text{PF}_6]_2$, the sample did not fly in the ESMS. $^1\text{H-NMR}$ spectra recorded in CD_2Cl_2 for $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$, all show broad peaks in the aromatic region suggesting that more than one species is present. As previously described [18,20,21] these dinuclear double stranded arrays can exist as helicate (rac-isomer) and box (meso-isomer) and these two are commonly interchanging in the NMR timescale leading to broad NMR peaks. The meso-isomer is usually the enthalpic product (the dominant solid state species) while the helicate is favoured entropically and is the major product in solution at room temperature [18,20,21]. In particular, $[\text{Cu}_2(\mathbf{3c})_2][\text{PF}_6]_2$, the NMR peaks were extremely broad making peak assignments difficult.

Liquid crystal properties of these free ligands **1a-d**, **2a-d**, **3a-c**, and **4a-d** and the three copper Cu (I) complexes $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$ were investigated using an OPM. Unfortunately, none of the compounds exhibited liquid crystalline phases. Possible reasons for this could lie in the ligands having too much flexibility about the central methylene unit. Secondly the two isomeric forms of the copper (I) complexes may prevent the molecules from becoming sufficiently ordered in the mesophase.

3. Experimental

3.1. General

The starting materials which were commercially available were purchased from Aldrich and used as received. The solvents were purchased from Fisher Scientific (CH_2Cl_2 , EtOAc, Et_2O and MeOH) or Aldrich (anhydrous EtOH). Solvents were either used as received or dried; DCM was distilled from CaCl_2 under a N_2 atmosphere. Yields refer to chromatographically pure products. Thin-layer

chromatography (TLC) was carried out on aluminum sheets coated with silica gel 60 (Merck 5554 mesh). Column chromatography was performed on silica gel 60 (Merck 230-400). Microanalyses were performed by the University of London microanalytical laboratories or by the University of Birmingham microanalytical services. Electron impact (EI) mass spectra were recorded at 70eV on a VG ProSpec mass spectrometer. Liquid secondary ion mass spectra (LSIMS) were recorded on a VG ZaBSpec mass spectrometer equipped with a cesium ion source and utilizing *m*-nitrobenzyl alcohol containing a trace of sodium acetate as the liquid matrix. ¹H-NMR spectra were recorded on a Bruker AC 300 (300 MHz) spectrometer. ¹³C-NMR spectra were recorded on a Bruker AC 300 (75.5 MHz) spectrometer. The chemical shift values are expressed as δ values and the coupling constant values (*J*) are in Hertz (Hz). The following abbreviations are used for the signal multiplicities or characteristics: s, singlet; d, doublet; dd, doublet of doublets; t, triplet; m, multiplet; q, quartet; quint; quintet; br, broad. Transition temperatures were measured using a Mettler FP82 HT hot stage and central processor in conjunction with Leitz DMFRT Polarizing microscope as well as differential scanning calorimetry (DSC7 Perkin-Elmer).

Methyl 3,4-dihydroxybenzoate (8): A solution of 3,4-dihydroxybenzoic acid (**6**, 15.00 g, 97.30 mmol) and conc. H₂SO₄ (1.5 mL) in MeOH (200 mL) was stirred and heated under reflux overnight. The resultant yellow solution was allowed to cool to room temperature and the solvent removed *in vacuo*, affording a brown solid (14.60 g, 82%). mp: 126-129 °C; ¹H-NMR (acetone-d₆): δ_{H} 8.55 (br s, 1H, OH), 7.50 (d, *J* = 2.0 Hz, 1H, Ar-H), 7.44 (dd, 1H, Ar-H, *J* = 8.3, 2.0 Hz), 6.90 (d, 1H, Ar-H, *J* = 8.3 Hz), 3.80 (s, 3H, OMe), 3.01 (br s, 1H, OH); ¹³C-NMR (acetone-d₆): δ_{C} 167.0, 150.7, 145.5, 123.2, 122.7, 117.0, 115.7, 51.8; MS *m/z* (EIMS): 168 ([M]⁺, 54%), 137 ([M-OMe]⁺, 100%), 109 ([M-CO₂Me]⁺, 20%); IR ν/cm^{-1} (nujol): 3468, 3263, 2927, 2854, 1690.

Methyl 3,4,5-trihydroxybenzoate (9): The same procedure as described for the preparation of **8** was followed, using 3,4,5-trihydroxybenzoic acid (**7**, 16.60 g, 97.40 mmol), conc. H₂SO₄ (0.5 mL) and MeOH (200 mL). This yielded a pale brown solid (14.40 g, 80%). mp: 120-124 °C; ¹H-NMR (acetone-d₆): δ_{H} 7.11 (s, 2H, Ar-H), 3.78 (s, 3H, OMe); ¹³C-NMR (acetone-d₆): δ_{C} 167.9, 146.7, 139.5, 122.5, 110.5, 49.3; MS *m/z* (EIMS): 184 ([M]⁺, 55%), 153 ([M-OMe]⁺, 100%), 125 ([M-CO₂Me]⁺, 17%); IR ν/cm^{-1} (nujol): 3468, 3263, 1690.

Methyl 3,4-dipentyloxybenzoate (10a): A suspension of K₂CO₃ (9.90 g, 71.63 mmol) in a solution of methyl 3,4-dihydroxybenzoate (**8**, 3.00 g, 17.84 mmol) and *n*-bromopentane (6.75 g, 44.69 mmol) in MeCN (100 mL) was stirred and heated under reflux overnight. The resultant brown mixture was allowed to cool to room temperature and concentrated *in vacuo* (30 mL). Water (250 mL) was added and the aqueous layer was extracted by washing with Et₂O (3 x 100 mL). The combined organic layers were washed with brine solution (50 mL), dried (MgSO₄), filtered and solvent removed *in vacuo*, yielding an orange oil as the crude product. The crude product was purified via silica gel column chromatography (gradient elution: 0 to 10 % EtOAc in hexane, increase polarity in increments of 5% per 150 mL of eluent used). The solvent was removed *in vacuo* to yield a colourless oil (4.84 g, 88%). ¹H-NMR (CDCl₃): δ_{H} 7.62 (dd, 1H, Ar-H, *J* = 8.5, 2.2 Hz), 7.53 (d, 1H, Ar-H, *J* = 2.2 Hz), 6.86 (d, 1H, Ar-H, *J* = 8.5 Hz), 4.05-4.02 (m, 4H, 2 x OCH₂), 3.88 (s, 3H, OMe), 1.89-1.79 (m, 4H, 2 x CH₂),

1.50-1.33 (m, 8H, 4 x CH₂), 0.87 (t, 6H, 2 x CH₃, *J* = 7.0 Hz); ¹³C-NMR (CDCl₃): δ_C 167.0, 153.1, 148.4, 123.5, 122.4, 114.1, 111.9, 69.2, 69.0, 51.9, 28.9, 28.2, 22.5, 14.1; MS *m/z* (EIMS): 308 ([M]⁺, 28 %), 168 ([M-(2 x C₅H₁₀)]⁺, 137 ([M-(2 x C₅H₁₀)-OMe]⁺, 24%); IR ν/cm⁻¹ (nujol): 2926, 2856, 1718.

Using the same general procedure as described for **10a**, the following compounds were prepared:

Methyl 3,4-diheptyloxybenzoate (10b): From K₂CO₃ (9.90 g, 71.63 mmol) methyl 3,4-dihydroxybenzoate (**8**, 3.00 g, 17.84 mmol) and *n*-bromoheptane (8.10 g, 45.23 mmol). This yielded a pale yellow oil (6.00 g, 92%). mp: 30-32 °C; ¹H-NMR (CDCl₃): δ_H 7.63 (dd, 1H, Ar-H, *J* = 8.5, 2.0 Hz), 7.53 (d, 1H, Ar-H, *J* = 2.0 Hz), 6.86 (d, 1H, Ar-H, *J* = 8.5 Hz), 4.05-4.03 (m, 4H, 2 x OCH₂), 3.88 (s, 3H, OMe), 1.85-1.80 (m, 4H, 2 x CH₂), 1.31-1.25 (m, 16H, 8 x CH₂), 0.88 (t, 6H, 2 x CH₃, *J* = 6.6 Hz); ¹³C-NMR (CDCl₃): δ_C 167.2, 153.3, 148.6, 123.7, 122.5, 114.3, 112.0, 69.4, 69.1, 52.1, 32.0, 29.2, 26.1, 22.8, 14.2; MS *m/z* (EIMS): 365 ([M+H]⁺, 100%); IR ν/cm⁻¹ (nujol): 2926, 2856, 1723.

Methyl 3,4-dinonyloxybenzoate (10c): From K₂CO₃ (9.90 g, 71.63 mmol), methyl 3,4-dihydroxybenzoate (**8**, 3.00 g, 17.84 mmol) and *n*-bromononane (9.26 g, 44.70 mmol). This yielded a white solid (6.64 g, 88%). mp: 36-38 °C ¹H-NMR (CDCl₃): δ_H 7.62 (dd, 1H, Ar-H, *J* = 8.5, 2.0 Hz), 7.52 (d, 1H, Ar-H, *J* = 2.0 Hz), 6.85 (d, 1H, Ar-H, *J* = 8.5 Hz), 4.05-4.03 (m, 4H, 2 x OCH₂), 3.87 (s, 3H, OMe), 1.88-1.76 (m, 4H, 2 x CH₂), 1.46-1.25 (m, 24H, 12 x CH₂), 0.87 (t, 6H, 2 x CH₃, *J* = 6.6 Hz); ¹³C-NMR (CDCl₃): δ_C 167.0, 153.2, 148.5, 123.5, 122.4, 114.2, 111.9, 69.3, 69.0, 51.9, 31.9, 29.6, 29.4, 29.3, 29.1, 26.0, 22.7, 14.1; MS *m/z* (EIMS): 420 ([M]⁺, 46%), 154 ([M-(2 x C₇H₁₄)]⁺, 100%); IR ν/cm⁻¹ (nujol): 2927, 2853, 1723.

Methyl 3,4-didodecanyloxybenzoate (10d): From K₂CO₃ (9.90 g, 71.63 mmol), methyl 3,4-dihydroxybenzoate (**8**, 3.00 g, 17.84 mmol) and *n*-bromododecane (11.12 g, 44.62 mmol). This yielded a white solid (6.81 g, 76%). mp: 46-48 °C; ¹H-NMR (CDCl₃): δ_H 7.62 (dd, 1H, Ar-H, *J* = 8.5, 2.0 Hz), 7.52 (d, 1H, Ar-H, *J* = 2.0 Hz), 6.85 (d, 1H, Ar-H, *J* = 8.5 Hz), 4.05-4.03 (m, 4H, 2 x OCH₂), 3.87 (s, 3H, OMe), 1.88-1.79 (m, 4H, 2 x CH₂), 1.47-1.27 (m, 36H, 18 x CH₂), 0.87 (t, 6H, 2 x CH₃, *J* = 6.6 Hz); ¹³C-NMR (CDCl₃): δ_C 167.0, 157.3, 148.5, 123.5, 122.4, 114.2, 111.9, 69.3, 69.0, 51.9, 32.0, 29.7, 29.4, 29.2, 29.1, 26.0, 22.7, 14.2; MS *m/z* (EIMS): 505 ([M+H]⁺, 100%); IR ν/cm⁻¹ (nujol): 2926, 2855, 1718.

Methyl 3,4,5-tripentyloxybenzoate (11a): From methyl 3,4,5-trihydroxybenzoate (**9**, 3.83 g, 20.83 mmol) and *n*-bromopentane (11.01 g, 72.91 mmol), K₂CO₃ (11.50 g, 83.3 mmol) and MeCN (100 mL). This yielded a pale yellow oil (5.07 g, 61%). ¹H-NMR (CDCl₃): δ_H 7.24 (s, 2H, Ar-H), 4.01 (t, 6H, 3 x OCH₂, *J* = 6.6 Hz), 3.88 (s, 3H, OMe), 1.86-1.69 (m, 6H, 3 x CH₂), 1.48-1.32 (m, 12H, 6 x CH₂), 0.92 (t, *J* = 7.0 Hz, 3H, CH₃), 0.91 (t, 6H, 2 x CH₃, *J* = 7.0 Hz); ¹³C-NMR (CDCl₃): δ_C 165.4, 151.3, 140.9, 123.0, 106.5, 71.9, 67.6, 50.5, 28.4, 27.4, 26.7, 21.0, 20.9, 12.5; MS *m/z* (EIMS): 394 ([M]⁺, 20%), 324 ([M-C₅H₁₀]⁺, 5%), 184 ([M-(3 x C₅H₁₀)]⁺, 100%); IR ν/cm⁻¹ (nujol): 2925, 2854, 1718.

Methyl 3,4,5-triheptyloxybenzoate (11b): From K_2CO_3 (9.90 g, 71.63 mmol) methyl 3,4,5-trihydroxybenzoate (**9**, 3.83 g, 20.82 mmol) and *n*-bromoheptane (13.04 g, 72.85 mmol). This yielded a yellow oil (5.97 g, 60%). 1H -NMR ($CDCl_3$): δ_H 7.24 (s, 2H, Ar-H), 4.00 (t, 6H, 3 x OCH_2 , $J = 6.6$ Hz), 3.88 (s, 3H, OMe), 1.85-1.68 (m, 6H, 3 x CH_2), 1.48-1.29 (m, 24H, 12 x CH_2), 0.88 (t, 9H, 3 x CH_3 , $J = 7.0$ Hz); ^{13}C -NMR ($CDCl_3$): δ_C 165.1, 151.0, 140.8, 122.9, 106.2, 71.6, 67.3, 50.2, 30.0, 28.5, 27.5, 27.3, 27.2, 24.2, 20.8, 12.2; MS m/z (EIMS): 478 ($[M]^+$, 72 %), 380 ($[M-C_7H_{14}]^+$, 25%), 184 ($[M-(3 \times C_7H_{14})]^+$, 100%); IR ν/cm^{-1} (nujol): 2930, 2870, 1723.

Methyl 3,4,5-trinonyloxybenzoate (11c): From K_2CO_3 (9.90 g, 71.63 mmol) methyl 3,4,5-trihydroxybenzoate (**9**, 3.83 g, 20.82 mmol) and *n*-bromononane (15.08 g, 72.85 mmol). This yielded a yellow oil (7.37 g, 63%). 1H -NMR ($CDCl_3$): δ_H 7.24 (s, 2H, Ar-H), 4.00 (t, 6H, 3 x OCH_2 , $J = 6.6$ Hz), 3.88 (s, 3H, OMe), 1.85-1.68 (m, 6H, 3 x CH_2), 1.48-1.27 (m, 36H, 18 x CH_2), 0.88 (t, 9H, 3 x CH_3 , $J = 7.0$ Hz); ^{13}C -NMR ($CDCl_3$): δ_C 165.8, 151.3, 140.9, 122.9, 106.8, 71.9, 67.7, 54.1, 33.9, 32.3, 31.6, 31.4, 31.3, 28.1, 24.7, 16.1; MS m/z (ESMS): 585 ($[M+Na]^+$, 100%); IR ν/cm^{-1} (nujol): 2930, 2871, 1723.

Methyl 3,4,5-tridodecyloxybenzoate (11d): From K_2CO_3 (9.90 g, 71.63 mmol) methyl 3,4,5-trihydroxybenzoate (**9**, 3.83 g, 20.82 mmol) and *n*-bromododecane (18.14 g, 72.85 mmol). This yielded a yellow oil (9.02 g, 63%). 1H -NMR ($CDCl_3$): δ_H 7.24 (s, 2H, Ar-H), 4.00 (t, 6H, 3 x OCH_2 , $J = 6.6$ Hz), 3.88 (s, 3H, OMe), 1.85-1.68 (m, 6H, 3 x CH_2), 1.48-1.29 (m, 54H, 27 x CH_2), 0.88 (t, 9H, 3 x CH_3 , $J = 6.99$ Hz); ^{13}C -NMR ($CDCl_3$): δ_C 166.2, 152.0, 141.2, 123.1, 107.2, 72.6, 68.3, 51.0, 31.0, 29.4, 28.2, 28.4, 28.1, 25.0, 21.8, 13.2; MS m/z (ESMS): 688 ($[M+Na]^+$, 100%); IR ν/cm^{-1} (nujol): 2930, 2870, 1723.

3,4-Dipentyloxybenzoic acid (12a): To a solution of methyl 3,4-dipentyloxybenzoate (**10a**, 4.84 g, 15.7 mmol) in MeOH (150 mL), an aqueous solution of sodium hydroxide (15 mL, 2.10 mol L^{-1}) was added and the mixture was stirred and heated under reflux overnight. The resultant colourless solution was allowed to cool to room temperature and HCl (2 M) was added dropwise to acidify the solution, whereupon a white precipitate was formed, which was filtered off. The filtrate was concentrated *in vacuo* (~20 mL) and water (100 mL) was added. The aqueous layer was extracted with Et_2OAc (3 x 100 mL). The combined organic layers were washed with brine solution (20 mL), dried ($MgSO_4$) and filtered. The solvent was removed *in vacuo*, yielding a white solid (4.00 g, 87%). mp: 126-128 $^{\circ}C$; 1H -NMR ($CDCl_3$): δ_H 7.72 (dd, 1H, Ar-H, $J = 8.5, 2.2$ Hz), 7.58 (d, 1H, Ar-H, $J = 2.2$ Hz), 6.89 (d, 1H, Ar-H, $J = 8.5$ Hz), 4.07-4.04 (m, 4H, 2 x OCH_2), 1.88-1.82 (m, 4H, 2 x CH_2), 1.49-1.38 (m, 8H, 4 x CH_2), 0.87 (t, 6H, 2 x CH_3 , $J = 6.6$ Hz); ^{13}C -NMR ($CDCl_3$): δ_C 171.7, 153.9, 148.5, 124.5, 121.4, 114.5, 111.8, 69.3, 69.0, 28.7, 28.2, 22.5, 14.1; MS m/z (EIMS): 294 ($[M]^+$, 25%), 224 ($[M-C_5H_{10}]^+$, 9%), 154 ($[M-(2 \times C_5H_{10})]^+$); IR ν/cm^{-1} (nujol): 2926, 2856, 2646, 1684.

Following the same general procedure described for **12a**, the following compounds were prepared:

3,4-Diheptyloxybenzoic acid (12b): From compound **11b** (5.94 g, 16.30 mmol) and sodium hydroxide (15 mL, 2.18 mol L^{-1}). This yielded a white solid (4.70 g, 82%). mp: 120-123 $^{\circ}C$; 1H -NMR ($CDCl_3$): δ_H 7.70 (dd, 1H, Ar-H, $J = 8.5, 2.2$ Hz), 7.56 (d, 1H, Ar-H, $J = 2.2$ Hz), 6.87 (d, 1H, Ar-H, $J = 8.5$ Hz),

4.05-4.02 (m, 4H, 2 x OCH₂), 1.83-1.81 (m, 4H, 2 x CH₂), 1.31-1.25 (m, 16H, 8 x CH₂), 0.88 (t, 6H, 2 x CH₃, $J = 6.6$ Hz); ¹³C-NMR (CDCl₃): δ_C 171.9, 153.7, 148.3, 124.3, 121.3, 114.3, 111.6, 69.1, 68.8, 31.0, 28.9, 25.8, 22.8, 13.9; MS m/z (EIMS): 351 ([M+H]⁺, 25%), 333 ([M-OH]⁺, 100%); IR ν/cm⁻¹ (nujol): 2925, 2855, 2646, 1670s.

3,4-Dinonyloxybenzoic acid (12c): From compound **10c** (6.42 g, 15.26 mmol) and sodium hydroxide (15 mL, 2.03 mol L⁻¹). This yielded a white solid (5.85 g, 94%). mp: 112-114 °C; ¹H-NMR (CDCl₃): δ_H 7.71 (dd, 1H, Ar-H, $J = 8.5, 2.2$ Hz), 7.52 (d, 1H, Ar-H, $J = 2.2$ Hz), 6.85 (d, 1H, Ar-H, $J = 8.5$ Hz), 4.07-4.03 (m, 4H, 2 x OCH₂), 1.87-1.79 (m, 4H, 2 x CH₂), 1.49-1.27 (m, 24H, 12 x CH₂), 0.87 (t, 6H, 2 x CH₃, $J = 6.6$ Hz); ¹³C-NMR (CDCl₃): δ_C 172.0, 154.1, 148.7, 124.7, 121.5, 114.6, 112.0, 69.4, 69.2, 32.1, 29.7, 29.6, 26.5, 26.2, 22.9, 14.3; MS m/z (EIMS): 406 ([M]⁺, 46%), 280 ([M-C₇H₁₄]⁺, 154 ([M-(2 x C₇H₁₄)]⁺, 100%); IR ν/cm⁻¹ (nujol): 2926, 2854, 2644, 1670.

3,4-Didodecanyloxybenzoic acid (12d): From compound **10d** (6.55 g, 12.98 mmol) and sodium hydroxide (15 mL, 1.87 mol L⁻¹). This yielded a white solid (5.64 g, 89%). mp: 106-109 °C; ¹H-NMR (CDCl₃): δ_H 7.71 (dd, 1H, Ar-H, $J = 8.5, 2.2$ Hz), 7.57 (d, 1H, Ar-H, $J = 2.2$ Hz), 6.88 (d, 1H, Ar-H, $J = 8.5$ Hz), 4.07-4.03 (m, 4H, 2 x OCH₂), 1.87-1.79 (m, 4H, 2 x CH₂), 1.52-1.26 (m, 36H, 18 x CH₂), 0.87 (t, 6H, 2 x CH₃, $J = 6.6$ Hz); ¹³C-NMR (CDCl₃): δ_C 172.1, 154.3, 148.8, 124.9, 121.6, 114.7, 112.1, 69.6, 69.4, 32.3, 29.9, 29.8, 26.5, 26.4, 26.2, 25.6, 22.9, 14.5; MS m/z (ESMS): 513 ([M+Na]⁺, 100%); IR ν/cm⁻¹ (nujol): 2926, 2854, 2644, 1670.

3,4,5-Tripentyloxybenzoic acid (13a): From compound **11a** (4.62 g, 11.73 mmol) and sodium hydroxide (15 mL, 2.18 mol L⁻¹). This yielded a white solid (4.46 g, 74%). mp: 48-50 °C; ¹H-NMR (CDCl₃): δ_H 7.12 (s, 2H, Ar-H), 3.89 (t, 2H, OCH₂, $J = 6.4$ Hz), 3.79 (t, 4H, 2 x OCH₂, $J = 5.9$ Hz), 1.61-1.69 (m, 6H, 3 x CH₂), 1.42-1.25 (m, 12H, 6 x CH₂), 0.89 (t, 3H, CH₃, $J = 7.0$ Hz), 0.85 (t, 6H, 2 x CH₃, $J = 6.8$ Hz); ¹³C-NMR (CDCl₃): δ_C 173.4, 153.5, 142.7, 127.4, 108.9, 74.1, 69.7, 31.0, 30.1, 29.3, 29.2, 23.5, 14.9; MS m/z (EIMS): 380 ([M]⁺, 25%), 170 ([M-(3 x C₅H₁₁)]⁺, 100 %); IR ν/cm⁻¹ (nujol): 2927, 2854, 2646, 1684.

3,4,5-Triheptyloxybenzoic acid (13b): From compound **11b** (5.50 g, 11.51 mmol) and sodium hydroxide (15 mL, 2.18 mol L⁻¹). This yielded a white solid (4.02 g, 76%). mp: 47-49 °C; ¹H-NMR (CDCl₃): δ_H 7.31 (s, 2H, Ar-H), 4.03 (t, 2H, OCH₂, $J = 6.6$ Hz), 4.01 (t, 4H, 2 x OCH₂, $J = 6.6$ Hz), 1.86-1.70 (m, 6H, 3 x CH₂), 1.52-1.29 (m, 24H, 12 x CH₂), 0.88 (t, 9H, 3 x CH₃, $J = 6.6$ Hz); ¹³C-NMR (CDCl₃): δ_C 173.8, 153.5, 142.9, 127.6, 109.0, 74.3, 69.8, 329, 32.8, 31.4, 30.4, 30.2, 27.2, 27.0, 23.6, 15.0; MS m/z (ESMS): 487 ([M+Na]⁺, 100%); IR ν/cm⁻¹ (nujol): 2926, 2854, 2646, 1670.

3,4,5-Trinonyloxybenzoic acid (13c): From compound **11c** (7.10 g, 12.63 mmol) and sodium hydroxide (15 mL, 1.68 mol dm⁻³). This yielded a white solid (5.40 g, 78%). mp: 47-49 °C; ¹H-NMR (CDCl₃): δ_H 7.30 (s, 2H, Ar-H), 4.03 (t, 2H, OCH₂, $J = 6.6$ Hz), 4.01 (t, 4H, 2 x OCH₂, $J = 6.6$ Hz), 1.86-1.69 (m, 6H, 3 x CH₂), 1.47-1.27 (m, 36H, 18 x CH₂), 0.87 (t, 9H, 3 x CH₃, $J = 6.6$ Hz); ¹³C-NMR (CDCl₃): δ_C

170.8, 150.8, 140.1, 121.6, 106.5, 71.5, 67.1, 29.8, 28.2, 27.6, 27.5, 27.3, 27.2, 24.0, 20.6, 12.0; MS m/z (ESMS): 547 ($[M-H]^-$, 100%); IR ν/cm^{-1} (nujol): 2928, 2855, 2647, 1670.

3,4,5-Tridodecyloxybenzoic acid (13d): From compound **11d** (8.80 g, 12.79 mmol) and sodium hydroxide (15 mL, 1.71 mol L⁻¹). This yielded a white solid (6.71 g, 81%). mp: 47-49 °C; ¹H-NMR (CDCl₃): δ_H 7.30 (s, 2H, Ar-H), 4.03 (t, 2H, OCH₂, $J = 6.6$ Hz), 4.01 (t, 4H, 2 x OCH₂, $J = 6.6$ Hz), 1.86-1.69 (m, 6H, 3 x CH₂), 1.47-1.25 (m, 54H, 27 x CH₂), 0.87 (t, 9H, 3 x CH₃, $J = 6.6$ Hz); ¹³C-NMR (CDCl₃): δ_C 171.3, 151.1, 141.1, 122.1, 106.8, 71.8, 67.4, 30.2, 28.6, 27.9, 27.6, 27.5, 24.3, 20.9, 12.3; MS m/z (ESMS): 697 ($[M+Na]^+$, 100%); IR ν/cm^{-1} (nujol): 2926, 2854, 1674s.

5-Hydroxy-2-methylpyridine N-oxide (15): A solution of 5-hydroxy-2-methylpyridine (**14**, 15.0 g, 0.14 mol) and hydrogen peroxide 27.5 % (33 mL, 0.27 mol) in CH₃CO₂H (300 mL) was heated at 80 °C for 2.5 hrs. A colour change of solution was observed from orange to pale yellow. The solution was further stirred at room temperature for 24 hrs and concentrated *in vacuo* (50 mL). Acetone (400 mL) was added to force precipitation. The resulting pale yellow precipitate was collected by vacuum filtration (12.7 g, 74%). mp: 188.9-189.5 °C (decomposes); ¹H-NMR (CD₃OD): δ_H 7.93 (d, 1H, Py-H, $J = 2.2$ Hz), 7.32 (d, 1H, Py-H, $J = 8.8$ Hz), 7.03 (dd, 1H, Py-H, $J = 8.8, 2.2$ Hz), 2.41 (s, 3H, CH₃); ¹³C-NMR (CD₃OD): δ_C 158.7, 144.3, 136.0, 130.6, 122.1, 19.1; MS m/z (EIMS): 125 ($[M]^+$, 50%), 109 ($[M-O]^+$, 100%); IR ν/cm^{-1} (nujol): 2924, 2854, 1840, 1612.

2-Pyridylmethanol acetate (16): 5-Hydroxy-2-methylpyridine N-oxide (**15**, 17.5 g, 0.14 mol) was slowly added to (CH₃CO)₂O (170 mL) at 110 °C. The resultant dark brown reaction mixture was stirred for 2 hrs at 140 °C. EtOH (400 mL) was added and the solution was concentrated *in vacuo* to yield brown oil. CHCl₃ (100 mL) was added and the solution was neutralised with saturated NaHCO₃. The organic layers were collected through washings with saturated NaHCO₃ (2 x 20 mL), dried (MgSO₄) and filtered. The solvent was removed *in vacuo* to yield a brown oil, which was further dried under high vacuum for 2 hrs (26.1 g, 89%). ¹H-NMR (CDCl₃): δ_H 8.40 (d, 1H, Py-H, $J = 2.6$ Hz), 7.49 (d, 1H, Py-H, $J = 8.5$ Hz), 7.39 (dd, 1H, Py-H, $J = 8.5, 2.6$ Hz), 5.21 (s, 2H, CH₂), 2.33 (s, 3H, CH₃), 2.15 (s, 3H, CH₃); ¹³C-NMR (CDCl₃): δ_C 170.7, 168.9, 152.9, 146.7, 143.0, 130.0, 122.5, 66.3, 22.2, 21.0; MS m/z (FABMS): 210 ($[MH]^+$, 100%); IR ν/cm^{-1} (nujol): 2923, 2854, 1747, 1582.

5-Hydroxy-2-hydroxymethylpyridine (17): A solution of 2-pyridylmethanol acetate (**16**) in conc. HCl (30 mL) was heated under reflux for 1.5 hrs. The reaction mixture was cooled to room temperature and concentrated *in vacuo*. CHCl₃ (200 mL) was added and the solution neutralised carefully with saturated NaHCO₃. The aqueous layers were collected through washings with saturated NaHCO₃ and concentrated *in vacuo*. The brown solid was triturated with MeOH (500 mL) and filtrates collected through filtration. The solvent was removed *in vacuo* yielding a brown solid (8.3 g, 98%). ¹H-NMR (CDCl₃): δ_H 7.85 (d, 1H, Py-H, $J = 2.6$ Hz), 7.18 (d, 1H, Py-H, $J = 8.5$ Hz), 7.01 (dd, 1H, Py-H, $J = 8.5, 2.6$ Hz), 4.51 (s, 2H, CH₂); ¹³C-NMR (CDCl₃): δ_C 163.5, 147.8, 141.5, 128.0, 124.8, 66.7; MS m/z (FABMS): 125 ($[M+H]^+$, 35%).

5-Hydroxypyridine 2-carbaldehyde (18): A suspension of 5-hydroxy-2-hydroxymethylpyridine (**17**, 2.50 g, 19.98 mmol) and activated MnO₂ (1.74 g, 19.98 mmol) in *iso*-PrOH (100 mL) was heated under reflux for 3 hrs. The hot mixture was filtered through Celite[®] and washed thoroughly with hot MeOH (400 mL). The solution was allowed to cool to room temperature and concentrated *in vacuo*, yielding a brown solid. The solid was absorbed onto silica and purified via short silica gel column chromatography (gradient elution: 0 to 5% methanol in CH₂Cl₂, increase polarity in increments of 2 % per 150 mL of eluent used). The solvent was removed *in vacuo* to yield a brown solid (1.41 g, 57%). mp: 223-225 °C (decomposes); ¹H-NMR (CD₃OD): δ_H 9.60 (s, 1H, CHO), 7.90 (d, 1H, Py-H, *J* = 2.2 Hz), 7.74 (d, 1H, Py-H, *J* = 8.8 Hz), 6.84 (dd, 1H, Py-H, *J* = 8.8, 2.2 Hz), ¹³C-NMR (CD₃OD): 193.0, 172.2, 146.5, 140.9, 130.2, 126.6; MS *m/z* (FABMS): 123 ([M]⁺, 50%), 109 ([M-CH₂], 27%), 95 ([M-CO]⁺, 100%); IR *v/cm*⁻¹ (nujol): 2923, 2854, 1668, 1507.

3,4-Bisdipentyloxybenzoic acid 6-formylpyridin-3-ester (19a): To a solution of 5-hydroxypyridine-2-carbaldehyde (**18**, 0.50 g, 2.44 mmol) in dry CH₂Cl₂ (30 mL), cooled in an ice bath under a N₂ atmosphere, compound **12a** (0.72 g, 2.44 mmol), 1-(3-dimethylaminopropyl)-3-ethylcarbodiimide hydrochloride (EDC) (1.16 g, 60.55 mmol) and 4-dimethylaminopyridine (catalytical amount) were added. The solution was stirred at room temperature under a N₂ atmosphere for 24 hrs. HCl (50 mL, 1 mol dm⁻³) was added, which yielded a white solid. MeOH (10 mL) was added to dissolve the precipitate. The organic layers were collected through washings with CH₂Cl₂ (3 x 30 mL), dried (MgSO₄) and filtered. The solvent was removed *in vacuo*, to yield a brown solid. The solid was absorbed onto silica and purified via silica gel column chromatography (gradient elution: 0 to 10 % EtOAc in hexane, increase polarity in increments of 5% per 150 mL of eluent used). The solvent was removed *in vacuo* to yield a white solid (0.35 g, 36%); mp: 63-66 °C; ¹H-NMR (CDCl₃): δ_H 10.09 (s, 1H, CHO), 8.71 (d, 1H, Py-H, *J* = 8.5 Hz), 8.07 (d, 1H, Py-H, *J* = 2.6 Hz), 7.83 (dd, 1H, Ar-H, *J* = 8.5, 2.2 Hz), 7.79 (dd, 1H, Py-H, *J* = 8.5, 2.6 Hz), 7.64 (d, 1H, Ar-H, *J* = 2.2 Hz), 6.94 (d, 1H, Ar-H, *J* = 8.5 Hz), 4.09 (t, 2H, OCH₂, *J* = 6.6 Hz), 4.07 (t, 2H, OCH₂, *J* = 6.6 Hz) 1.92-1.82 (m, 4H, 2 x CH₂), 1.48-1.39 (m, 8H, 4 x CH₂), 0.94 (t, 3H, CH₃, *J* = 7.0 Hz), 0.93 (t, 3H, CH₃, *J* = 7.0 Hz); ¹³C-NMR (CDCl₃): δ_C 192.1, 164.8, 155.4, 151.89, 150.8, 149.7, 145.0, 131.0, 125.7, 123.4, 120.9, 115.5, 112.8, 70.2, 70.0, 29.6, 29.5, 29.0, 23.3, 14.8; MS *m/z* (ESMS): 399 ([M]⁺, 20%), 277 ([M-OpyCO]⁺, 100%); IR *v/cm*⁻¹ (nujol): 2924, 2854, 1728.

Following the same general procedure described for **19a**, the following compounds were prepared:

3,4-Bisdiheptyloxybenzoic acid 6-formylpyridin-3-ester (19b): From compound **18** (0.50 g, 2.44 mmol), compound **12b** (0.85 g, 2.44 mmol) and EDC (1.16 g, 60.55 mmol) in dry CH₂Cl₂ (50 mL) to yield a white solid (0.40 g, 40%); mp: 66-68 °C; ¹H-NMR (CDCl₃): δ_H 10.08 (s, 1H, CHO), 8.70 (d, 1H, Py-H, *J* = 2.6 Hz), 8.07 (d, 1H, Py-H, *J* = 8.5 Hz), 7.82 (dd, 1H, Ar-H, *J* = 8.5, 2.2 Hz), 7.79 (dd, 1H, Py-H, *J* = 8.5, 2.6 Hz), 7.64 (d, 1H, Ar-H, *J* = 2.2 Hz), 6.95 (d, 1H, Ar-H, *J* = 8.5 Hz), 4.09 (t, 2H, OCH₂, *J* = 6.6 Hz), 4.06 (t, 2H, OCH₂, *J* = 6.6 Hz), 1.89-1.83 (m, 4H, 2 x CH₂), 1.49-1.30 (m, 16H, 8 x CH₂), 0.89-0.84 (m, 6H, 2 x CH₃); ¹³C-NMR (CDCl₃): δ_C 192.2, 164.6, 152.7, 149.1, 148.1, 147.0,

142.3, 128.3, 123.0, 120.7, 118.2, 112.8, 110.1, 67.6, 67.3, 29.9, 27.3, 27.1, 24.1, 20.7, 12.2; MS m/z (FABMS): 478 ($[M+Na]^+$, 25%); IR ν/cm^{-1} (nujol): 2925, 2854, 1728.

3,4-Bisdinonyloxybenzoic acid 6-formylpyridin-3-ester (19c): From compound **18** (0.50 g, 2.44 mmol), compound **12c** (0.99 g, 2.44 mmol) and EDC (1.16 g, 60.55 mmol) in dry CH_2Cl_2 (50 mL). This yielded a white solid (0.45 g, 36%); mp: 68-70 °C; 1H -NMR ($CDCl_3$): δ_H 10.08 (s, 1H, CHO), 8.71 (d, 1H, Py-H, $J = 2.2$ Hz), 8.07 (d, 1H, Py-H, $J = 8.5$ Hz), 7.83 (dd, 1H, Ar-H, $J = 8.5, 2.2$ Hz), 7.79 (dd, 1H, Py-H, $J = 8.5, 2.2$ Hz), 7.64 (d, 1H, Ar-H, $J = 2.2$ Hz), 6.94 (d, 1H, Ar-H, $J = 8.5$ Hz), 4.09 (t, 2H, OCH_2 , $J = 6.6$ Hz), 4.06 (t, 2H, OCH_2 , $J = 6.6$ Hz), 1.89-1.82 (m, 4H, 2 x CH_2), 1.49-1.28 (m, 24H, 12 x CH_2), 0.89-0.85 (m, 6H, 2 x CH_3); ^{13}C -NMR ($CDCl_3$): δ_C 192.1, 162.5, 153.7, 149.5, 148.5, 147.4, 142.7, 128.7, 123.4, 121.1, 118.6, 113.2, 110.5, 68.0, 67.7, 30.4, 28.1, 27.9, 27.8, 27.5, 24.5, 21.2, 12.6; MS m/z (ESMS): 534 ($[M+Na]^+$, 85%); IR ν/cm^{-1} (nujol): 2930, 2855, 1730.

3,4-Bisdidodecyloxybenzoic acid 6-formylpyridin-3-ester (19d): From compound **18** (0.50 mg, 2.44 mmol), compound **12d** (1.20 g, 2.44 mmol) and EDC (1.16 g, 60.55 mmol) in dry CH_2Cl_2 (50 mL). This yielded a white solid (0.46 g, 32%); mp: 70-71 °C; 1H -NMR ($CDCl_3$): δ_H 10.09 (s, 1H, CHO), 8.71 (d, 1H, Py-H, $J = 2.6$ Hz), 8.71 (d, 1H, Py-H, $J = 8.5$ Hz), 7.83 (dd, 1H, Ar-H, $J = 8.5, 2.2$ Hz), 7.79 (dd, 1H, Py-H, $J = 8.5, 2.6$ Hz), 7.64 (d, 1H, Ar-H, $J = 2.2$ Hz), 6.95 (d, 1H, Ar-H, $J = 8.5$ Hz), 4.09 (t, 2H, OCH_2 , $J = 6.6$ Hz), 4.07 (t, 2H, OCH_2 , $J = 6.6$ Hz), 1.96-1.82 (m, 4H, 2 x CH_2), 1.49-1.26 (m, 36H, 18 x CH_2), 0.87 (t, 6H, 2 x CH_3 , $J = 6.6$ Hz); ^{13}C -NMR ($CDCl_3$): δ_C 192.1, 164.0, 154.5, 150.9, 149.9, 148.8, 144.2, 130.2, 124.8, 122.5, 120.0, 114.5, 111.9, 69.4, 69.1, 31.9, 29.6, 29.4, 29.1, 26.0, 22.7, 14.1; MS m/z (ESMS): 618 ($[M+Na]^+$, 100%); IR ν/cm^{-1} (nujol): 2929, 2856, 1731.

3,4,5-Trispentyloxybenzoic acid 6-formylpyridin-3-ester (20a): From compound **18** (0.50 g, 4.07 mmol), compound **13a** (1.55 g, 4.07 mmol) and EDC (1.16 g, 6.06 mmol) in dry CH_2Cl_2 (50 mL). This yielded a brown oil (0.77 g, 40%); 1H -NMR ($CDCl_3$): δ_H 10.09 (s, 1H, CHO), 8.70 (d, 1H, Py-H, $J = 2.6$ Hz), 8.08 (d, 1H, Py-H, $J = 8.5$ Hz), 7.77 (dd, 1H, Py-H, $J = 8.5, 2.6$ Hz), 7.39 (s, 2H, Ar-H), 4.07 (t, 2H, OCH_2 , $J = 6.6$ Hz), 4.04 (t, 4H, 2 x OCH_2 , $J = 6.6$ Hz) 1.89-1.72 (m, 6H, 3 x CH_2), 1.50-1.26 (m, 12H, 6 x CH_2), 0.93 (t, 9H, 3 x CH_3 , $J = 7.0$ Hz); ^{13}C -NMR ($CDCl_3$): δ_C 192.2, 164.2, 153.3, 151.1, 150.3, 144.4, 144.0, 130.4, 122.8, 122.6, 109.0, 73.8, 69.6, 30.1, 29.1, 28.4, 22.6, 22.5, 14.1; MS m/z (EIMS): 485 ($[M]^+$, 15%), 363 ($[M-OPyCHO]^+$, 100%), 293 ($[M-OPyCHO-C_5H_{10}]^+$, 75%), 153 ($[M-OPyCHO-(3xC_5H_{10})]^+$, 30%); IR ν/cm^{-1} (nujol): 2927, 2854, 1728.

3,4,5-Trisheptyloxybenzoic acid 6-formylpyridin-3-ester (20b): From compound **18** (0.50 g, 4.07 mmol), compound **13b** (1.89 g, 4.07 mmol) and EDC (1.16 g, 6.06 mmol) in dry CH_2Cl_2 (50 mL). This yielded a brown oil (0.88 g, 39%); 1H -NMR ($CDCl_3$): δ_H 10.09 (s, 1H, CHO), 8.70 (d, 1H, Py-H, $J = 2.6$ Hz), 8.07 (d, 1H, Py-H, $J = 8.5$ Hz), 7.77 (dd 1H, Py-H, $J = 8.5, 2.6$ Hz), 7.39 (s, 2H, Ar-H), 4.06 (t, 2H, OCH_2 , $J = 6.6$ Hz), 4.06 (t, 4H, 2 x OCH_2 , $J = 6.6$ Hz), 1.88-1.71 (m, 6H, 3 x CH_2), 1.50-1.30 (m, 24H, 12 x CH_2), 0.88 (t, 9H, 3 x CH_3 , $J = 6.4$ Hz); ^{13}C -NMR ($CDCl_3$): δ_C 192.4, 164.4, 153.5, 151.3, 150.5, 144.5, 144.2, 130.6, 122.9, 122.8, 109.2, 74.0, 69.7, 32.3, 32.2, 29.6, 29.4, 26.4, 23.0, 14.4; MS m/z (ESMS): 592 ($[M+Na]^+$, 100%); IR ν/cm^{-1} (nujol): 2926, 2854, 1728.

3,4,5-Bistrinonyloxybenzoic acid 6-formylpyridin-3-ester (20c): From compound **18** (0.50 g, 4.07 mmol), compound **13c** (2.23 g, 4.07 mmol) and EDC (1.16 g, 60.55 mmol) in dry CH₂Cl₂ (50 mL). This yielded a white solid (0.89 g, 34%); mp: 34-37 °C; ¹H-NMR (CDCl₃): δ_H 10.08 (s, 1H, CHO), 8.69 (d, 1H, Py-H, *J* = 2.6 Hz), 8.07 (d, 1H, Py-H, *J* = 8.5 Hz), 7.77 (dd, 1H, Py-H, *J* = 8.5, 2.6 Hz), 7.39 (s, 2H, Ar-H), 4.07 (t, 2H, OCH₂, *J* = 6.4 Hz), 4.04 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 1.87-1.71 (m, 6H, 3 x CH₃), 1.50-1.26 (m, 36H, 18 x CH₂), 0.87 (t, 3H, CH₃, *J* = 6.6 Hz), 0.86 (t, 6H, 2 x CH₃, *J* = 7.0 Hz); ¹³C-NMR (CDCl₃): δ_C 194.7, 166.7, 155.8, 153.6, 152.8, 146.8, 146.5, 132.9, 125.3, 125.1, 111.5, 76.3, 72.0, 34.5, 33.0, 32.3, 32.2, 32.0, 28.7, 25.3, 16.7; MS *m/z* (ESMS): 676 ([M+Na]⁺, 100%); IR ν/cm⁻¹ (nujol): 2927, 2855, 1730.

3,4,5-Trisdodecyloxybenzoic acid 6-formylpyridin-3-ester (20d): From compound **18** (0.50 g, 4.07 mmol), compound **13d** (2.74 g, 2.44 mmol) and EDC (1.16 g, 60.55 mmol) in dry CH₂Cl₂ (50 mL). This yielded a white solid (0.89 g, 35%); mp: 41-43 °C: ¹H-NMR (CDCl₃): δ_H 10.08 (s, 1H, CHO), 8.69 (d, 1H, Py-H, *J* = 2.2 Hz), 8.07 (d, 1H, Py-H, *J* = 8.5 Hz), 7.77 (dd, 1H, Py-H, *J* = 8.5, 2.2 Hz), 7.39 (s, 2H, Ar-H), 4.06 (t, 2H, OCH₂, *J* = 6.6 Hz), 4.04 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 1.85-1.71 (m, 6H, 3 x CH₂), 1.49-1.25 (m, 54H, 27 x CH₂), 0.86 (t, 9H, 3 x CH₃, *J* = 6.6 Hz); ¹³C-NMR (CDCl₃): δ_C 191.3, 163.3, 152.4, 150.2, 149.4, 143.4, 143.1, 129.4, 121.8, 121.6, 108.1, 72.9, 68.6, 31.2, 29.6, 28.8, 28.6, 25.3, 21.9, 13.3; MS *m/z* (ESMS): 802 ([M+Na]⁺, 100%), 780 ([M+H]⁺, 20%); IR ν/cm⁻¹ (nujol): 2927, 2856, 1731.

6-{N-[4-({4-[(E)-[(5-[[3, 4-bis (pentyloxy) phenyl]carbonyloxy}pyridin-2-yl)methylidene]amino]phenyl)methyl]phenyl]carboximidoyl}pyridin-3-yl 3,4-bis(pentyloxy)benzoate (1a): To a solution of compound **19a** (202 mg, 0.51 mmol) in anhydrous EtOH (4 mL) under N₂ atmosphere, 4,4'-methylene dianiline (50 mg, 0.25 mmol) was added. The reaction mixture was stirred and heated at 50 °C for 24 hrs under a N₂ atmosphere. The solid was collected through suction filtration and recrystallised in anhydrous PhMe. The yellow solid was collected through suction filtration (140 mg, 58%); mp: 158-159 °C; Calculated for C₅₉H₆₈N₄O₈: 73.72% C, 7.13% H, 5.83% N; found: 73.68% C, 7.10% H, 5.90% N; ¹H-NMR (CDCl₃): δ_H 8.63 (s, 2H, HC=N), 8.62 (d, 2H, Py-H, *J* = 2.2 Hz), 8.28 (d, 2H, Py-H, *J* = 8.5 Hz), 7.83 (dd, 2H, Ar-H, *J* = 8.5, 1.8 Hz), 7.71 (dd, 2H, Py-H, *J* = 8.5, 2.2 Hz), 7.65 (d, 2H, Ar-H, *J* = 1.8 Hz), 7.26 (s, 8H, Ar-H), 6.94 (d, 2H, Ar-H, *J* = 8.5 Hz), 4.09 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 4.07 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 4.05 (s, 2H, Ph₂CH₂), 1.90-1.81 (m, 8H, 4 x CH₂), 1.55-1.34 (m, 16H, 8 x CH₂), 0.94 (t, 6H, 2 x CH₃, *J* = 7.0 Hz), 0.93 (t, 6H, 2 x CH₃, *J* = 7.0 Hz); ¹³C-NMR (CDCl₃): δ_C, 166.8, 161.5, 156.8, 154.4, 151.1, 151.4, 145.9, 142.3, 132.5, 132.3, 132.1, 127.2, 124.9, 123.9, 123.0, 117.1, 114.5, 71.9, 71.6, 43.5, 31.3, 31.2, 30.7, 24.5, 16.5; MS *m/z* (ESMS): 962 ([M+H]⁺, 100%); IR ν/cm⁻¹ (nujol): 2927, 2854, 1729, 1598.

Following the same general procedure described for the preparation of **1a**, the following compounds were prepared:

6-{N-[4-({4-[(E)-[(5-[[3,4-bis(heptyloxy)phenyl]carbonyloxy}pyridin-2-yl)methylidene]amino]phenyl)methyl]phenyl]carboximidoyl}pyridin-3-yl 3,4-bis(heptyloxy)benzoate (1b): From compound **19b** (230 mg, 0.51 mmol), 4,4'-methylenedianiline (50 mg, 0.25 mmol) and anhydrous EtOH (4 mL).

This yielded a pale yellow solid (186 mg, 69%); mp: 136-137 °C; Calculated for C₆₇H₈₄N₄O₈: 74.97% C, 7.89% H, 5.22% N; found: 74.88% C, 7.70% H, 5.18% N; ¹H-NMR (CDCl₃): δ_H 8.63 (s, 2H, HC=N), 8.62 (d, 2H, Py-H, *J* = 2.6 Hz), 8.28 (d, 2H, Py-H, *J* = 8.5 Hz), 7.83 (dd, 2H, Ar-H, *J* = 8.5, 2.1 Hz), 7.71 (dd, 2H, Py-H, *J* = 8.5, 2.6 Hz), 7.65 (d, 2H, Ar-H, *J* = 2.1 Hz), 7.26 (s, 8H, Ar-H), 6.94 (d, 2H, Ar-H, *J* = 8.5 Hz), 4.09 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 4.07 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 4.04 (s, 2H, Ph₂CH₂), 1.91-1.80 (m, 8H, 4 x CH₂), 1.55-1.34 (m, 32H, 16 x CH₂), 0.89 (t, 6H, 2 x CH₃, *J* = 6.99 Hz), 0.88 (t, 6H, 2 x CH₃, *J* = 6.99 Hz); ¹³C-NMR (CDCl₃): δ_C 165.5, 160.1, 155.5, 153.1, 150.1, 150.0, 144.5, 140.9, 131.2, 130.9, 130.7, 125.8, 123.5, 122.5, 121.6, 115.8, 113.1, 70.5, 70.3, 42.2, 32.9, 30.3, 30.2, 27.1, 23.7, 15.2; MS m/z (ESMS): 1096 ([M+Na]⁺, 100%); IR ν/cm⁻¹ (nujol): 2926, 2855, 1729, 1598.

6-*N*-[4-({4-[(*E*)-[(5-{{3,4-bis(nonyloxy)phenyl}carbonyloxy}pyridin-2-yl)methylidene]amino-phenyl)methyl}phenyl]carboximidoyl}pyridin-3-yl 3,4-bis(nonyloxy)benzoate (**1c**): From compound **19c** (258 mg, 0.51 mmol), 4,4'-methylenedianiline (50 mg, 0.25 mmol) and anhydrous EtOH (5 mL). This yielded a pale yellow solid (155 mg, 52%); mp: 129 °C; Calculated for C₇₅H₁₀₀N₄O₈: 75.98% C, 8.50% H, 4.73% N; found: 75.80% C, 8.40% H, 4.63% N; ¹H-NMR (CDCl₃): δ_H 8.63 (s, 2H, HC=N), 8.62 (d, 2H, Py-H, *J* = 2.6 Hz), 8.29 (d, 2H, Py-H, *J* = 8.8 Hz), 7.83 (dd, 2H, Ar-H, *J* = 8.5, 1.8 Hz), 7.71 (dd, 2H, Py-H, *J* = 8.8, 2.6 Hz), 7.65 (d, 2H, Ar-H, *J* = 1.8 Hz), 7.26 (s, 8H, Ar-H), 6.94 (d, 2H, Ar-H, *J* = 8.5 Hz), 4.09 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 4.07 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 4.05 (s, 2H, CH₂), 1.89-1.80 (m, 8H, 4 x CH₂), 1.49-1.29 (m, 48H, 24 x CH₂), 0.88 (t, 6H, 2 x CH₃, *J* = 7.0 Hz), 0.87 (t, 6H, 2 x CH₃, *J* = 7.0 Hz); ¹³C-NMR (CDCl₃): δ_C 166.0, 160.7, 156.0, 155.2, 153.6, 150.6, 150.5, 145.0, 141.4, 131.7, 131.4, 126.4, 124.0, 123.1, 122.1, 116.3, 113.6, 71.1, 70.8, 42.8, 33.5, 31.2, 31.0, 30.9, 30.8, 30.7, 27.6, 24.3, 15.7; MS m/z (ESMS): 1207 ([M+Na]⁺); IR ν/cm⁻¹ (nujol): 2926, 2854, 1727, 1598.

6-*N*-[4-({4-[(*E*)-[(5-{{3,4-bis(dodecyloxy)phenyl}carbonyloxy}pyridin-2-yl)methylidene]amino-phenyl)methyl}phenyl]carboximidoyl}pyridin-3-yl 3,4-bis(dodecyloxy)benzoate (**1d**): From compound **19d** (301 mg, 0.51 mmol), 4,4'-methylenedianiline (50 mg, 0.25 mmol) and anhydrous EtOH (6 mL). This yielded a pale yellow solid (190 mg, 56%); mp: 126 °C; Calculated for C₈₇H₁₂₄N₄O₈: 77.18% C, 9.23% H, 4.14% N; found: 77.23% C, 9.31% H, 4.17% N; ¹H-NMR (CDCl₃): δ_H 8.63 (s, 2H, HC=N), 8.62 (d, 2H, Py-H, *J* = 2.6 Hz), 8.29 (d, 2H, Py-H, *J* = 8.8 Hz), 7.83 (dd, 2H, Ar-H, *J* = 8.5, 1.8 Hz), 7.71 (dd, 2H, Py-H, *J* = 8.8, 2.6 Hz), 7.65 (d, 2H, Ar-H, *J* = 1.8 Hz), 7.26 (s, 8H, Ar-H), 6.94 (d, 2H, Ar-H, *J* = 8.5 Hz), 4.09 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 4.07 (t, 4H, 2 x OCH₂, *J* = 6.6 Hz), 4.05 (s, 2H, Ph₂CH₂), 1.89-1.80 (m, 8H, 4 x CH₂), 1.49-1.29 (m, 72H, 36 x CH₂), 0.88 (t, 6H, 2 x CH₃, *J* = 7.0 Hz), 0.87 (t, 6H, 2 x CH₃, *J* = 7.0 Hz); ¹³C-NMR (CDCl₃): δ_C 165.5, 160.2, 155.6, 154.7, 153.1, 150.2, 150.1, 144.2, 141.0, 131.3, 131.1, 126.4, 123.6, 122.7, 121.7, 115.7, 110.0, 71.1, 70.8, 42.8, 33.5, 31.2, 31.0, 30.9, 30.8, 30.7, 27.6, 24.3, 15.7; MS m/z (ESMS): 1354 ([M]⁺, 100%); IR ν/cm⁻¹ (nujol): 2927, 2854, 1727, 1597.

6-*N*-[4-({4-[(*E*)-[(5-{{3,4,5-tris(pentyloxy)phenyl}carbonyloxy}pyridin-2-yl)methylidene]amino-phenyl)methyl}phenyl]carboximidoyl}pyridin-3-yl 3,4,5-tris(pentyloxy)benzoate (**2a**): From compound **20a** (245 mg, 0.51 mmol), 4,4'-methylenedianiline (50 mg, 0.25 mmol) and anhydrous EtOH (4 mL). This yielded a yellow solid (151 mg, 53%). mp: 67 °C; Calculated for C₆₉H₈₈N₄O₁₀: 73.12% C, 7.83%

H, 4.94% N; found: 73.16% C, 7.87% H, 4.89% N; $^1\text{H-NMR}$ (CDCl_3): δ_{H} 8.63 (s, 2H, HC=N), 8.61 (d, 2H, Py-H, $J = 2.6$ Hz), 8.29 (d, 2H, Py-H, $J = 8.8$ Hz), 7.71 (dd, 2H, Py-H, $J = 8.8, 2.6$ Hz), 7.41 (s, 4H, Ar-H), 7.26 (s, 8H, Ar-H), 4.07 (t, 4H, 2 x OCH_2 , $J = 6.6$ Hz), 4.05 (t, 8H, 4 x OCH_2 , $J = 6.6$ Hz), 4.05 (s, 2H, Ph_2CH_2), 1.89-1.72 (m, 12H, 6 x CH_2), 1.53-1.31 (m, 24H, 12 x CH_2), 0.93 (t, 18H, 6 x CH_3 , $J = 7.0$ Hz); $^{13}\text{C-NMR}$ (CDCl_3): δ_{C} 164.7, 159.3, 153.4, 152.4, 149.3, 149.1, 143.9, 143.7, 140.2, 130.4, 130.2, 123.2, 122.7, 121.8, 109.1, 74.0, 69.7, 41.5, 31.3, 29.3, 28.6, 22.9, 22.8, 14.4; MS m/z (ESMS): 1133 ($[\text{M}]^+$); IR ν/cm^{-1} (nujol): 2930, 2857, 1743, 1587.

6- $\{N$ -[4-({4-[(*E*)-[(5-{{3,4,5-tris(heptyloxy)phenyl}carbonyloxy}pyridin-2-yl)methylidene]amino}phenyl)methyl]phenyl]carboximidoyl}pyridin-3-yl 3,4,5-tris(heptyloxy)benzoate (**2b**): From compound **20b** (287 mg, 0.51 mmol), 4,4'-methylenedianiline (50 mg, 0.25 mmol) and anhydrous EtOH (4 mL). This yielded a yellow solid (197 mg, 60%); mp: 54-56 °C; Calculated for $\text{C}_{81}\text{H}_{112}\text{N}_4\text{O}_{10}$: 74.73% C, 8.67% H, 4.30% N; found: 74.78% C, 8.70% H, 4.32% N; $^1\text{H-NMR}$ (CDCl_3): δ_{H} 8.63 (s, 2H, HC=N), 8.61 (d, 2H, Py-H, $J = 2.6$ Hz), 8.29 (d, 2H, Py-H, $J = 8.5$ Hz), 7.70 (dd, 2H, Py-H, $J = 8.5, 2.6$ Hz), 7.40 (s, 4H, Ar-H), 7.26 (s, 8H, Ar-H), 4.07 (t, 4H, 2 x OCH_2 , $J = 6.4$ Hz), 4.05 (t, 8H, 4 x OCH_2 , $J = 6.3$ Hz), 4.05 (s, 2H, Ph_2CH_2), 1.88-1.71 (m, 12H, 6 x CH_2), 1.50-1.27 (m, 48H, 12 x CH_2), 0.88 (t, 6H, 2 x CH_3 , $J = 6.6$ Hz), 0.87 (t, 12H, 4 x CH_3 , $J = 7.0$ Hz); $^{13}\text{C-NMR}$ (CDCl_3): δ_{C} 163.1, 157.7, 151.9, 150.1, 147.7, 147.6, 142.4, 142.2, 138.6, 128.8, 128.6, 121.6, 121.2, 120.2, 107.6, 72.4, 68.2, 39.9, 30.7, 30.6, 29.1, 28.1, 28.0, 27.8, 24.8, 21.4, 12.9; MS m/z (ESMS): 1302 ($[\text{M}+\text{H}]^+$); IR ν/cm^{-1} (nujol): 2930, 2857, 1744s, 1590.

6- $\{N$ -[4-({4-[(*E*)-[(5-{{3,4,5-tris(nonyloxy)phenyl}carbonyloxy}pyridin-2-yl)methylidene]amino}phenyl)methyl]phenyl]carboximidoyl}pyridin-3-yl 3,4,5-tris(nonyloxy)benzoate (**2c**): From compound **20c** (330 mg, 0.51 mmol), 4,4'-methylenedianiline (50 mg, 0.25 mmol) and anhydrous EtOH (5 mL). This yielded a yellow solid (241 mg, 65%); mp: 60-62 °C; Calculated for $\text{C}_{93}\text{H}_{136}\text{N}_4\text{O}_{10}$: 75.98% C, 9.32% H, 3.81% N; found: 75.90% C, 9.27% H, 3.85% N; $^1\text{H-NMR}$ (CDCl_3): δ_{H} 8.63 (s, 2H, HC=N), 8.61 (d, 2H, Py-H, $J = 2.6$ Hz), 8.29 (d, 2H, Py-H, $J = 8.5$ Hz), 7.70 (dd, 2H, Py-H, $J = 8.5, 2.6$ Hz), 7.40 (s, 4H, Ar-H), 7.26 (s, 8H, Ar-H), 4.07 (t, 4H, 2 x OCH_2 , $J = 6.6$ Hz), 4.05 (t, 8H, 4 x OCH_2 , $J = 6.6$ Hz), 4.05 (s, 2H, CH_2), 1.88-1.71 (m, 12H, 6 x CH_2), 1.50-1.21 (m, 72H, 36 x CH_2), 0.88 (t, 6H, 2 x CH_3 , $J = 7.0$ Hz), 0.87 (t, 12H, 4 x CH_3 , $J = 7.0$ Hz); $^{13}\text{C-NMR}$ (CDCl_3): δ_{C} 164.4, 159.0, 153.1, 152.1, 149.0, 148.8, 143.6, 143.4, 139.9, 130.1, 129.8, 122.8, 122.4, 121.4, 108.8, 73.7, 69.4, 41.4, 31.9, 30.4, 29.7, 29.6, 29.4, 29.3, 26.1, 22.7, 14.1; MS m/z (ESMS): 1471 ($[\text{M}+\text{H}]^+$); IR ν/cm^{-1} (nujol): 2930, 2857, 1744, 1589.

6- $\{N$ -[4-({4-[(*E*)-[(5-{{3,4,5-tris(dodecyloxy)phenyl}carbonyloxy}pyridin-2-yl)methylidene]amino}phenyl)methyl]phenyl]carboximidoyl}pyridin-3-yl 3,4,5-tris(dodecyloxy)benzoate (**2d**): From compound **20d** (398 mg, 0.51 mmol), 4,4'-methylenedianiline (50 mg, 0.25 mmol) and anhydrous EtOH (6 mL). This yielded a yellow solid (291 mg, 67%); mp 51 °C; Calculated for $\text{C}_{111}\text{H}_{172}\text{N}_4\text{O}_{10}$: 77.40% C, 10.06% H, 3.25% N; found: 77.33% C, 10.01% H, 3.27% N; $^1\text{H-NMR}$ (CDCl_3): δ_{H} 8.63 (s, 2H, HC=N), 8.61 (d, 2H, Py-H, $J = 2.6$ Hz), 8.29 (d, 2H, Py-H, $J = 8.8$ Hz), 7.70 (dd, 2H, Py-H, $J = 8.8, 2.6$ Hz), 7.40 (s, 4H, Ar-H), 7.27 (s, 8H, Ar-H), 4.06 (t, 4H, 2 x OCH_2 , $J = 6.4$ Hz), 4.04 (t, 8H, 4 x OCH_2 , $J = 6.3$ Hz), 4.04 (s, 2H, Ph_2CH_2), 1.89-1.71 (m, 12H, 6 x CH_2), 1.48-1.25 (m, 108H, 54 x

CH₂), 0.87 (t, 18H, 9 x CH₂, *J* = 6.6 Hz); ¹³C-NMR (CDCl₃): δ_C 162.5, 157.1, 151.2, 150.2, 147.1, 146.9, 141.7, 141.5, 138.0, 128.2, 128.0, 120.9, 120.5, 119.6, 106.9, 71.8, 67.5, 30.1, 28.5, 27.8, 27.5, 24.2, 20.8, 12.3; MS *m/z* (ESMS): 1744 ([M+Na]⁺); IR ν/cm⁻¹ (nujol): 2930, 2857, 1729, 1598.

6-*N*-[3-({3-[(*E*)-[(5-[[3,4-bis(pentyloxy)phenyl]carbonyloxy]pyridin-2-yl)methylidene]amino]-phenyl)methyl]phenyl]carboximidoyl]pyridin-3-yl 3,4-bis(pentyloxy)benzoate (**3a**): From compound **19a** (60 mg, 0.16 mmol), 3,3'-methylenedianiline (10 mg, 0.08 mmol) and anhydrous EtOH (2 mL). This yielded a brown oil (60 mg, 85%). ¹H-NMR (CDCl₃): δ_H 8.61 (s, 2H, HC=N), 8.60 (d, 2H, Py-H, *J* = 2.3 Hz), 8.27 (d, 2H, Py-H, *J* = 8.7 Hz), 7.82 (dd, 2H, Ar-H, *J* = 8.5, 2.1 Hz), 7.71 (dd, 2H, Py-H, *J* = 8.7, 2.3 Hz), 7.65 (d, 2H, Ar-H, *J* = 2.1 Hz), 7.35 (t, 2H, Ar-H, *J* = 8.5 Hz), 7.15 (m, 6H, Ar-H), 6.94 (d, 2H, Ar-H, *J* = 8.5 Hz), 4.07 (m, 10H, Ph₂CH₂, OCH₂), 1.88-1.68 (m, 8H, 4 x CH₂), 1.52-1.31 (m, 16H, 8 x CH₂), 0.93 (t, 12H, 4 x CH₃, *J* = 7.0 Hz); ¹³C-NMR (CDCl₃): δ_C 160.0, 152.2, 151.5, 149.3, 143.8, 142.4, 130.6, 130.5, 128.8, 127.9, 125.1, 122.8, 122.4, 120.9, 119.2, 115.0, 112.3, 42.2, 29.2, 29.1, 28.6, 22.9, 14.4; MS *m/z* (+ve FAB): 961 ([M]⁺, 80%).

6-*N*-[3-({3-[(*E*)-[(5-[[3,4-bis(heptyloxy)phenyl]carbonyloxy]pyridin-2-yl)methylidene]amino]-phenyl)methyl]phenyl]carboximidoyl]pyridin-3-yl 3,4-bis(heptyloxy)benzoate (**3b**): From compound **19b** (50 mg, 0.11 mmol), 3,3'-methylenedianiline (10 mg, 0.06 mmol) and anhydrous EtOH (2 mL). This yielded a brown oil (40 mg, 76%). ¹H-NMR (CDCl₃): δ_H 8.61 (s, 2H, HC=N), 8.61 (d, 2H, Py-H, *J* = 2.5 Hz), 8.27 (d, 2H, Py-H, *J* = 8.6 Hz), 7.83 (dd, *J* = 2H, Ar-H, 8.3, 2.0 Hz), 7.71 (dd, *J* = 2H, Py-H, 8.6, 2.3 Hz), 7.65 (d, 2H, Ar-H, *J* = 2.0 Hz), 7.35 (t, 2H, Ar-H, 7.5 Hz), 7.16-7.13 (m, 6H, Ar-H), 6.94 (d, 2H, Ar-H, *J* = 8.3 Hz), 4.09-4.05 (m, 10H, Ph₂CH₂, 4 x OCH₂), 1.88-1.71 (m, 8H, 4 x CH₂), 1.52-1.30 (m, 32H, 16 x CH₂), 0.93 (m, 12H, 4 x CH₃); ¹³C-NMR (CDCl₃): δ_C 160.0, 143.8, 130.5, 129.8, 127.8, 125.1, 122.8, 122.4, 119.1, 115.0, 112.4, 32.2, 29.6, 29.4, 26.4, 26.3, 23.0, 14.5; MS *m/z* (+ve FAB): 1073 ([M]⁺); IR ν/cm⁻¹ (nujol): 2911, 2851, 1729, 1598.

6-*N*-[3-({3-[(*E*)-[(5-[[3,4-bis(dodecyloxy)phenyl]carbonyloxy]pyridin-2-yl)methylidene]amino]-phenyl)methyl]phenyl]carboximidoyl]pyridin-3-yl 3,4-bis(dodecyloxy)benzoate (**3c**): From compound **19d** (70 mg, 0.12 mmol), 3,3'-methylenedianiline (10 mg, 0.06 mmol) and anhydrous EtOH (2 mL). This yielded a white solid (70 mg, 83%); Calculated for C₈₇H₁₂₄N₄O₈·H₂O: 76.2% C, 9.1% H, 4.1% N; found: 75.9% C, 9.0% H, 3.9% N; ¹H-NMR (CDCl₃): δ_H 8.60 (s, 2H, CHN), 8.61 (d, 2H, Py-H, *J* = 2.0 Hz), 8.27 (d, 2H, Py-H, *J* = 8.6 Hz), 7.83 (dd, *J* = 2H, Ar-H, 8.6, 2.0 Hz), 7.71 (d, 2H, Py-H, *J* = 8.3, 2.0 Hz), 7.65 (d, 2H, Ar-H, *J* = 2.0 Hz), 7.65 (s, 2H, Ar-H), 7.34 (t, 2H, Ar-H, *J* = 7.6 Hz), 7.16-7.13 (m, 6H, Ar-H), 6.94 (d, 2H, Ar-H, *J* = 8.6 Hz), 4.09 (m, 10H, Ph₂CH₂, 4 x OCH₂), 1.88-1.71 (m, 8H, 4 x CH₂), 1.48-1.27 (m, 72H, 36 x CH₂), 0.93 (t, 12H, 4 x CH₃, *J* = 7.0 Hz); MS *m/z* (+ve FAB): 1354 ([M]⁺); IR ν/cm⁻¹ (nujol): 2933, 2840, 1734, 1685, 1593, 1516.

6-*N*-[3-({3-[(*E*)-[(5-[[3,4,5-tris(pentyloxy)phenyl]carbonyloxy]pyridin-2-yl)methylidene]amino]-phenyl)methyl]phenyl]carboximidoyl]pyridin-3-yl 3,4,5-tris(pentyloxy)benzoate (**4a**): From compound **20a** (79 mg, 0.16 mmol), 3,3'-methylenedianiline (16 mg, 0.08 mmol) and anhydrous EtOH (2 mL). This yielded a brown oil (52 mg, 56%); Calculated for C₆₉H₈₈N₄O₁₀: 73.12% C, 7.83% H, 4.94% N; found: 73.16% C, 7.87% H, 4.89% N; ¹H-NMR (CDCl₃): δ_H 8.60 (s, 2H, HC=N), 8.60 (d, 2H, Py-H, *J*

= 2.6 Hz), 8.28 (d, 2H, Py-H, $J = 8.6$ Hz), 7.70 (dd, 2H, Py-H, $J = 8.6, 2.6$ Hz), 7.40 (s, 4H, Ar-H), 7.35 (t, 2H, Ar-H, $J = 7.7$ Hz), 7.16-7.13 (m, 6H, Ar-H), 4.07 (s, 2H, Ph₂CH₂), 4.07 (t, 4H, 2 x OCH₂, $J = 6.6$ Hz), 4.04 (t, 8H, 4 x OCH₂, $J = 6.6$ Hz), 1.88-1.68 (m, 12H, 6 x CH₂), 1.52-1.31 (m, 24H, 12 x CH₂), 0.92 (t, 18H, 6 x CH₃, $J = 6.99$ Hz); ¹³C-NMR (CDCl₃): δ_C 165.1, 161.3, 154.9, 153.7, 152.9, 150.6, 145.3, 145.1, 143.8, 131.8, 131.2, 129.2, 124.2, 123.8, 123.7, 120.5, 110.5, 75.4, 71.1, 43.6, 31.8, 30.7, 30.0, 24.3, 24.2, 15.8; MS m/z (ESMS): 1133 ([M]⁺, 100%); IR ν/cm⁻¹ (nujol): 2927, 2854, 1736, 1587.

6-*N*-[3-({3-[(*E*)-[(5-{[3,4,5-tris(heptyloxy)phenyl]carbonyloxy}pyridin-2-yl)methylidene]amino]-phenyl)methyl]phenyl]carboximidoyl]pyridin-3-yl 3,4,5-tris(heptyloxy)benzoate (**4b**): From compound **20b** (287 mg, 0.51 mmol), 3,3'-methylene dianiline (50 mg, 0.25 mmol) and anhydrous EtOH (4 mL). This yielded a brown oil (195 mg, 59%); Calculated for C₈₁H₁₁₂N₄O₁₀ 74.73% C, 8.67% H, 4.30% N; found: 74.78% C, 8.70% H, 4.32% N; ¹H-NMR (CDCl₃): δ_H 8.60 (s, 2H, HC=N), 8.60 (d, 2H, Py-H, $J = 2.6$ Hz), 8.28 (d, 2H, Py-H, $J = 8.6$ Hz), 7.70 (dd, 2H, Py-H, $J = 8.6, 2.6$ Hz), 7.40 (s, 4H, Ar-H), 7.35 (t, 2H, Ar-H, $J = 7.7$ Hz), 7.16-7.13 (m, 6H, Ar-H), 4.07 (s, 2H, Ph₂CH₂), 4.07 (t, 4H, 2 x OCH₂, $J = 6.6$ Hz), 4.04 (t, 8H, 4 x OCH₂, $J = 6.6$ Hz), 1.88-1.71 (m, 12H, 6 x CH₂), 1.52-1.30 (m, 48H, 24 x CH₂), 0.88 (t, 18H, 6 x CH₃, $J = 7.0$ Hz); ¹³C-NMR (CDCl₃): δ_C 164.8, 159.9, 153.5, 152.4, 151.5, 149.2, 144.0, 143.8, 142.4, 130.5, 129.8, 127.9, 123.2, 122.8, 122.4, 119.1, 109.2, 74.0, 69.8, 42.2, 32.3, 32.2, 30.8, 29.7, 29.6, 29.4, 26.4, 23.0, 14.5; MS m/z (ESMS): 1324 ([M+Na]⁺), 1303; IR ν/cm⁻¹ (nujol): 2927, 2854, 1739, 1586.

6-*N*-[3-({3-[(*E*)-[(5-{[3,4,5-tris(nonyloxy)phenyl]carbonyloxy}pyridin-2-yl)methylidene]amino]-phenyl)methyl]phenyl]carboximidoyl]pyridin-3-yl 3,4,5-tris(nonyloxy)benzoate (**4c**): From compound **20c** (160 mg, 0.25 mmol), 3,3'-methylenedianiline (24 mg, 0.12 mmol) and anhydrous EtOH (4 mL). This yielded a white solid (117 mg, 65%); mp: 51 °C; Calculated for C₉₃H₁₃₆N₄O₁₀ 75.98% C, 9.32% H, 3.81% N; found: 75.90% C, 9.37% H, 3.85% N; ¹H-NMR (CDCl₃): δ_H 8.60 (s, 2H, CHN), 8.60 (d, 2H, Py-H, $J = 2.2$ Hz), 8.28 (d, 2H, Py-H, $J = 8.6$ Hz), 7.69 (dd, 2H, Py-H, $J = 8.6, 2.2$ Hz), 7.40 (s, 4H, Ar-H), 7.35 (t, 2H, Ar-H, $J = 7.7$ Hz), 7.16-7.13 (m, 6H, Ar-H), 4.06 (s, 2H, Ph₂CH₂), 4.06 (t, 4H, 2 x OCH₂, $J = 6.6$ Hz), 4.04 (t, 8H, 4 x OCH₂, $J = 6.6$ Hz), 1.88-1.71 (m, 12H, 6 x CH₂), 1.48-1.27 (m, 72H, 36 x CH₂), 0.88 (t, 6H, 2 x CH₃, $J = 7.0$ Hz), 0.87 (t, 12H, 4 x CH₃, $J = 7.0$ Hz); ¹³C-NMR (CDCl₃): δ_C 163.6, 158.7, 152.3, 151.2, 150.3, 148.0, 142.8, 142.6, 141.3, 129.3, 128.6, 126.7, 122.0, 121.6, 121.2, 118.0, 108.0, 72.8, 68.6, 41.0, 31.1, 29.6, 28.9, 28.8, 28.6, 28.5, 25.3, 21.9, 13.3; MS m/z (ESMS): 1471 ([M+H]⁺); IR ν/cm⁻¹ (nujol): 2927, 2854, 1738, 1587.

6-*N*-[3-({3-[(*E*)-[(5-{[3,4,5-tris(dodecyloxy)phenyl]carbonyloxy}pyridin-2-yl)methylidene]amino]-phenyl)methyl]phenyl]carboximidoyl]pyridin-3-yl 3,4,5-tris(dodecyloxy)benzoate (**4d**): From compound **20d** (150 mg, 0.19 mmol), 3,3'-methylenedianiline (19 mg, 0.10 mmol) and anhydrous EtOH (4 mL). This yielded a white solid (110 mg, 67 %); mp: 55 °C; Calculated for C₁₁₁H₁₇₂N₄O₁₀ 77.40% C, 10.06% H, 3.25% N; found: 77.33% C, 10.01% H, 3.27% N; ¹H-NMR (CDCl₃): δ_H 8.60 (s, 2H, CHN), 8.60 (d, 2H, Py-H, $J = 2.6$ Hz), 8.29 (d, 2H, Py-H, $J = 8.5$ Hz), 7.69 (dd, 2H, Py-H, $J = 8.5, 2.6$ Hz), 7.40 (s, 4H, Ar-H), 7.35 (t, 2H, Ar-H, $J = 7.7$ Hz), 7.16-7.14 (m, 6H, Ar-H), 4.06 (s, 2H, Ph₂CH₂), 4.06 (t, 4H, 2 x OCH₂, $J = 6.6$ Hz), 4.07 (t, 8H, 4 x OCH₂, $J = 6.6$ Hz), 1.87-1.71 (m, 12H, 6

x CH₂), 1.48-1.25 (m, 108H, 54 x CH₂), 0.87 (t, 18H, 6 x CH₃, *J* = 6.6 Hz); ¹³C-NMR (CDCl₃): δ_C 164.3, 159.4, 153.0, 151.9, 151.0, 148.7, 143.5, 143.3, 142.0, 130.0, 129.3, 127.4, 122.7, 122.3, 122.0, 118.7, 108.7, 73.6, 69.3, 41.7, 31.9, 30.3, 29.6, 29.3, 26.0, 22.6, 14.0; MS *m/z* (ESMS): 1744 [(M+Na)]⁺; IR ν/cm⁻¹ (nujol): 2927, 2854, 1735, 1585.

[Cu₂(**3a**)₂][PF₆]₂: To a solution of compound **3a** (25 mg, 0.026 mmol) in propan-2-ol (5 mL) under a nitrogen atmosphere, [Cu(MeCN)₄][PF₆] (10 mg, 0.026 mmol) was added to give a dark red solution, which was heated under reflux overnight and then cooled to room temperature. A dark red solid precipitated from the solution on standing and was collected by filtration and washed with diethyl ether (41 mg, 67 %); Calculated for Cu₂C₁₁₈H₁₃₆N₈O₁₆P₂F₁₂·H₂O: 59.7% C, 5.9% H, 4.7% N; found: 59.4% C, 5.9%, 5.0% N; ¹H-NMR (CD₂Cl₂): δ_H 9.04 (br, 4H, HC=N), 8.46 (br, 4H, Py-H), 8.25 (br, 4H, Py-H), 8.08 (d, 4H, Ar-H, *J* = 8.0 Hz), 7.79 (d, 4H, Py-H, *J* = 8.6 Hz), 7.60 (s, 4H, Ar-H), 7.27 (t br, 4 H, Ar-H, *J* = 8.6 Hz), 7.00 (s br, 12H, Ar-H), 6.96 (d, 4H, Ar-H, *J* = 8.5 Hz), 4.09 (t, 8H, 4 x OCH₂, *J* = 6.5 Hz), 4.04 (t, 8H, 4 x OCH₂, *J* = 6.5 Hz), 3.69 (br s, 4H, Ph₂CH₂), 1.88-1.68 (m, 16H, 8 x CH₂), 1.52-1.31 (m, 32H, 16 x CH₂), 0.96 (q, 24H, 12 x CH₃, *J* = 7.0 Hz); *m/z* (+ve FABMS): 2194 [(Cu₂(**3a**)₂(PF₆)]⁺; MS *m/z* (ESMS): 1024 [(Cu₂(**3a**)₂)²⁺]; IR ν/cm⁻¹ (solid): 2953, 2926, 2867, 1727, 1594, 1556, 1521; UV/Vis (CH₂Cl₂) λ_{max} (ε, L mol⁻¹ cm⁻¹): 495 (9,500), 312 (83,600) nm.

[Cu₂(**3b**)₂][PF₆]₂: The same procedure as described for the preparation of compound [Cu₂(**3a**)₂][PF₆]₂ was followed, using compound **3b** (12 mg, 0.011 mmol) and [Cu(MeCN)₄][PF₆] (4 mg, 0.011 mmol). This yielded a dark red solid (20 mg, 70 %); ¹H-NMR (CD₂Cl₂): δ_H 9.03 (br s, 4H, HC=N), 8.53 (br s, 4H, Py-H), 8.23 (d, 4H, Py-H, *J* = 8.3 Hz), 8.08 (d, *J* = 4H, Ar-H, 8.3 Hz), 7.77 (d, 4H, Py-H, *J* = 8.5 Hz), 7.59 (s, 4H, Ar-H), 7.25 (br t, 4H, *J* = 7.5 Hz), 7.00 (s br, 12H, Ar-H), 6.98 (br s, 4H, Ar-H), 4.08 (t, 8H, 4 x OCH₂, *J* = 6.5 Hz), 4.02 (t, 8H, 4 x OCH₂, *J* = 6.5 Hz), 3.66 (br s, 4H, Ph₂CH₂), 1.88-1.71 (m, 16H, 4 x CH₂), 1.52-1.30 (m, 64H, 32 x CH₂), 0.90 (m, 24H, 12 x CH₃); *m/z* (+ve FAB MS): 2419 [Cu₂(**3b**)₂(PF₆)]⁺, 1137 [Cu(**3b**)]⁺; MS *m/z* (ESI MS): [Cu₂(**3b**)₂]²⁺; IR ν/cm⁻¹ (solid): 2922, 2852, 1727, 1595, 1556, 1513; UV/Vis (CH₂Cl₂) λ_{max} (ε, L mol⁻¹ cm⁻¹): 480 (11,400), 294 (94,600) nm.

[Cu₂(**3c**)₂][PF₆]₂: The same procedure as described for the preparation of compound [Cu₂(**3a**)₂][PF₆]₂ was followed, using compound **3c** (24 mg, 0.018 mmol) and [Cu(MeCN)₄][PF₆] (7 mg, 0.018 mmol). This yielded a dark red solid (56 mg, 65 %); The ¹H-NMR spectrum of the red material was very broad and the sample did not ionise well in ESI-MS; IR ν/cm⁻¹ (solid): 2919, 2853, 1732, 1662, 1600, 1508; UV/Vis (CH₂Cl₂) λ_{max} (ε, L mol⁻¹ cm⁻¹): 482 (7 400), 298 (94 700) nm.

4. Conclusions

In summary, we have successfully synthesised a series of novel banana-shaped compounds, in which the bend unit is formed by a 4,4'-methylenedianiline or 3,3'-methylenedianiline core bearing two symmetric pyridylimine linkages. Also, a number of complexes [Cu₂(**3a-c**)₂][PF₆]₂ were formed by coordination with Cu(I) cations. Mass spectrometry techniques have shown that dinuclear double stranded arrays were formed. Thermal analyses of the ligands **1a-d**, **2a-d**, **3a-c** and **4a-d** and the metal

complexes $[\text{Cu}_2(\mathbf{3a-c})_2][\text{PF}_6]_2$ revealed that these do not display any mesophase behavior. However, the generic structure of the target series **1a-d**, **2a-d**, **3a-c** and **4a-d** appears to fulfill, in principle, the same criteria of the banana-shaped mesogens known to date [37]. Further work is being carried out to prepare and investigate the liquid crystalline properties of the Cu (I) complexes formed from ligands **1a-d**, **2a-d** and **4a-d**, because such metal containing structures conjure up potential application of magnetic LC phases.

Acknowledgments

This research has been supported by the (i) Leverhulme Trust (MM), (ii) Perkin-Elmer/HEFCE in the UK through the Joint Research Equipment Initiative (JREI) and (iii) University of Warwick (LJC).

References and Notes

1. Niori, T.; Sekine, T.; Watanabe, J.; Fukawa, T.; Takezoe, H. Distinct Ferroelectric Smectic Liquid Crystals Consisting of Achiral Molecules with Banana Shape. *Mol. Cryst. Liq. Cryst.* **1997**, *301*, 337-342.
2. Sekine, T.; Takanishi, Y.; Niori, T.; Watanabe, J.; Takezoe, T. Spontaneous Helix Formation in Smectic Liquid Crystals Comprising Achiral Molecules. *J. Mater. Chem.* **1997**, *7*, 1307-1309.
3. Matsunaga, Y.; Miyamoto, S. Mesomorphic Behavior of 2,4-Bis-(4-alkoxybenzylidene) Cyclopentanones and Related Compounds. *Mol. Cryst. Liq. Cryst.* **1993**, *237*, 311-317.
4. Cai, R.; Samulski, E. New Thermotropic Liquid Crystals Derived from Thiophene. *Liq. Cryst.*, **1991**, *9*, 617-634.
5. Niori, T.; Sekine, T.; Watanabe, T.; Furukawa, J.; Takezoe, H. Distinct Ferroelectric Smectic Liquid Crystals Consisting of Banana Shaped Achiral Molecules. *J. Mater. Chem.* **1996**, *6*, 1231-1233.
6. Weissflog, W.; Lischka, C.H.; Kruth, H. Proceeding of the European Conference on Liquid Crystals, Science and Technology, Zakopane, Poland, December 10-11, **1997**, Volume 3-8, pp. 126-132.
7. Pelzl, G.; Diele, S.; Weissflog, W. Banana-Shaped Compounds – A New Field of Liquid Crystals. *Adv. Mater.* **1999**, *11*, 707-724.
8. Vill, V. *Landolt-Bornstein: Numerical data and functional relationship in science and technology, New Series*; Heidelberg: Berlin, Germany, 1992-1997.
9. Galyametdino, Y.G.; Ovchinnikov, I.V. Complexes of Liquid Crystal O-hydroxyazo Compounds with Cu^{2+} and Pd^{2+} Ions. *Russ. Chem. Bull.* **1991**, *40*, 2505-2508.
10. Hudson, S.A.; Maitlis, P.M. Metallogens. Synthesis, Properties and Applications. *Chem. Rev.* **1993**, *93*, 861-873.
11. Turanov, A.N.; Ovchinnikov, I.V.; Galyametdino, Y.G.; Ivanova, G.I.; Goncharo, V.A. Magnetic Anisotropy of Liquid Crystals Based on Lanthanide Mesogenic Complexes. *Russ. Chem. Bull.* **1999**, *48*, 690-693.
12. Bruce, D.W.; Liu, X.-H. Liquid Crystalline Complexes of Octahedral Manganese (I). *Chem. Commun.* **1994**, 729-730.

13. Rowe, K.E; Bruce, D.W. The Synthesis and Mesomorphism of Di-, Tetra- and Hexa-Catenar Liquid Crystals Based on 2, 2'-Bipyridine. *J. Mater. Chem.* **1998**, *8*, 331-341.
14. Liu, X.-H.; Henrich, B.; Manners, I.; Guillon, D., Bruce, D.W. The Synthesis, Mesomorphism and Mesophase Structure of Anisotropic Imines and their Complexes with Rhenium (I). *J. Mater. Chem.* **2000**, *10*, 637-644.
15. Fazio, D.; Mongin, C.; Donnio, B.; Galerne, Y.; Guillon, D., Bruce, D.W. Bending and Shaping: Cubics, Calamitics and Columnars. *J. Mater. Chem.* **2001**, *11*, 2852-2863.
16. Donnio, B.; Bruce, D.W. Metallomesogens. In *Structure and Bonding*, Mingos, D.M.P., Ed.; Springer-Verlag: Heidelberg, Berlin, Germany, 1999; Volume 95, Chapter 5, p. 193.
17. El-ghayoury, A.; Douce, L.; Skoulios, A.; Ziessel, R. Cation-Induced Macroscopic Ordering of Non-Mesomorphic Modules—A New Application for Metallohelicates. *Angew. Chem. Int. Ed.* **1998**, *37*, 2205-2208.
18. Hannon, M.J.; Painting, C.L.; Jackson, A.; Hamblin, J.; Errington, W. An Inexpensive Approach to Supramolecular Architecture. *Chem. Commun.* **1997**, 1807-1808.
19. Childs, L.J.; Hannon, M.J. Helices and Helicates, *Supramolecular Chem.* **2004**, *16*, 7-12.
20. Childs, L.J., Alcock, N.W., Hannon, M.J., Assembly of Nano-Scale Circular Supramolecular Arrays through π - π aggregation of Arc-Shaped Helicate Units. *Angew. Chem. Intl. Ed.* **2001**, *40*, 1079-1081
21. Childs, L.J., Pascu, M., Clarke, A.J., Alcock, N.W., Hannon, M.J. Using Non-Covalent Intra-Strand and Inter Strand Interactions to Prescribe Helix Formation within a Metallo-Supramolecular System. *Chem. Eur. J.* **2004**, *10*, 4291-4300.
22. Pelzl, G.; Diele, S.; Jakli, A.; Lischka, C.H.; Wirth, I.; Weissflog, W. Helical Superstructures in a Novel Smectic Mesophase Formed by Achiral Banana-Shaped Molecules. *Liq. Cryst.* **1999**, *26*, 135-139.
23. Shen, D.; Diele, S.; Pelzl, G.; Wirth, I.; Tschierske, C. Designing Banana-Shaped Liquid Crystals without Schiff's Base Units: m-Terphenyls, 2,6-Diphenylpyridines and V-Shaped Tolane Derivatives. *J. Mater. Chem.* **1991**, *9*, 661-672.
24. Shen, D.; Tschierske, C.; Diele, S.; Wirth, I. A Novel Class of Non-Chiral Banana-Shaped Liquid Crystals with Ferroelectric Properties. *Chem. Commun.* **1998**, 2573-2574.
25. Pelzl, G.; Diele, S.; Grande, S.; Jakli, A.; Lischka, C.H.; Kresse, H.; Schmalfuss, H.; Wirth, I.; Weissflog, W. Structural and Electro-Optical Investigations of the Smectic Phase of Chlorine-Substituted Banana-Shaped Compounds. *Liq. Cryst.* **1999**, *26*, 401-413.
26. Levitsky, I.A.; Kishikawa, K.; Eichhorn, S.H; Swagger, T.M. Exciton Coupling and Dipolar Correlations in a Columnar Liquid Crystal: Photophysics of a Bent-Rod Hexacatenar Mesogen. *J. Am. Chem. Soc.* **2000**, *122*, 2474-2479.
27. Weissflog, W.; Lischka, C.; Benne, I.; Scharf, T.; Pelzl, G.; Diele, S.; Kruth, H. *Proc. SPIE: Int. Soc. Opt. Eng.* **1998**, *14*, 3319-3321.
28. Dingemans, T.J.; Samulski, E.T. Non-Linear Boomerang-Shaped Liquid Crystals Derived from 2,5-Bis(p-hydroxyphenyl)-1,3,4-Oxadiazole. *Liq. Cryst.* **2000**, *27*, 131-136.
29. Matraszek, J.; Mieczkowski, J.; Szydłowska, J.; Gorecka, E. Nematic Phase Formed by Banana-Shaped Molecules. *Liq. Cryst.* **2000**, *27*, 429-436.

30. Shen, D.; Pegenau, A.; Diele, S.; Wirth, I.; Tschierske, C. Molecular Design of Non-Chiral Bent-Core Liquid Crystals with Antiferroelectric Properties. *J. Am. Chem. Soc.* **2000**, *122*, 1593-1601.
31. Thisayukta, J.; Nakayama, Y.; Kawauchi, H.; Takezoe, H.; Wantanabe, J. Distinct Formation of a Chiral Smectic Phase in Achiral Banana-Shaped Molecules with a Central Core Based on a 2,7-Dihydroxynaphthalene Unit. *J. Am. Chem. Soc.* **2000**, *122*, 7441-7448.
32. Heppke, G.; Parghi, D.D.; Sawade, H. Novel Sulphur-Containing Banana-Shaped Liquid Crystal Molecules. *Liq. Cryst.* **2000**, *27*, 313-320.
33. Kovalenko, L.; Weissflog, W.; Granda, S.; Diele, S.; Pelzl, G.; Wirth, I. Dimorphism SmA-B₂ in Bent-Core Mesogens with Perfluorinated Terminal Chains. *Liq. Cryst.* **2000**, *27*, 683-687.
34. Thisayukta, J.; Nakayama, Y.; Kawauchi, H.; Wantanabe, J. Effect of Chemical Structure on the Liquid Crystallinity of Banana-Shaped Molecules. *Liq. Cryst.* **2000**, *27*, 1129-1135.
35. Fatiadi, A.J. Active Manganese Dioxide Oxidation in Organic Chemistry. *Synthesis* **1976**, 65-104.
36. Belloni, M.; Manickam, M.; Preece, J. A. Towards Banana-Shaped Liquid Crystals Incorporating Carbazole. *Ferroelectrics* **2002**, *276*, 103-138.
37. Bedel, J.P.; Rouillon, J.C.; Marcerou, J.P.; Laguerre, M.; Achard, M.F.; Nguyen, H.T. Novel Mesophases in Fluorine Substituted Banana-Shaped Mesogens. *Liq. Cryst.* **2000**, *27*, 1411-1421.

© 2009 by the authors; licensee Molecular Diversity Preservation International, Basel, Switzerland. This article is an open-access article distributed under the terms and conditions of the Creative Commons Attribution license (<http://creativecommons.org/licenses/by/3.0/>).