

Original citation:

Shen, Ping, Zhang, Lifeng, Wang, Yi, Sridhar, Seetharaman and Wang, Qiangqiang. (2016) Wettability between molten slag and dolomitic refractory. *Ceramics International*, 42 (14). pp. 16040-16048.

Permanent WRAP URL:

<http://wrap.warwick.ac.uk/81098>

Copyright and reuse:

The Warwick Research Archive Portal (WRAP) makes this work by researchers of the University of Warwick available open access under the following conditions. Copyright © and all moral rights to the version of the paper presented here belong to the individual author(s) and/or other copyright owners. To the extent reasonable and practicable the material made available in WRAP has been checked for eligibility before being made available.

Copies of full items can be used for personal research or study, educational, or not-for-profit purposes without prior permission or charge. Provided that the authors, title and full bibliographic details are credited, a hyperlink and/or URL is given for the original metadata page and the content is not changed in any way.

Publisher's statement:

© 2016, Elsevier. Licensed under the Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International <http://creativecommons.org/licenses/by-nc-nd/4.0/>

A note on versions:

The version presented here may differ from the published version or, version of record, if you wish to cite this item you are advised to consult the publisher's version. Please see the 'permanent WRAP URL' above for details on accessing the published version and note that access may require a subscription.

For more information, please contact the WRAP Team at: wrap@warwick.ac.uk

Wettability between Molten Slag and Dolomitic Refractory

Ping Shen¹, Lifeng Zhang¹, Yi Wang¹, Seetharaman Sridhar², Qiangqiang Wang¹

¹School of Metallurgical and Ecological Engineering
University of Science and Technology Beijing
Beijing 100083, China

²Warwick Manufacturing Group, University of Warwick
Coventry, CV4 7AL, UK

Correspondent: Lifeng Zhang; tel.: +86-10-62332267; fax: +86-10-62332267; E-mail:
zhanglifeng@ustb.edu.cn;

postal address: School of Metallurgical and Ecological Engineering, University of Science and
Technology Beijing, No. 30, Xueyuan Road, Haidian District, Beijing 100083, China

ABSTRACT In the current study, the wettability between molten slag and dolomitic refractory materials used in the ladle during steel refining was investigated. The contact angle between molten slag and dolomitic substrate decreased with increasing temperature. The slag with lower basicity spread on the substrate more easily and penetrated deeper into the substrate. The penetration depth of slag into the refractory increased with the extension of holding time. The CaO in the refractory dissolved into slag which was then saturated with CaO. The reaction between slag and substrate resulted in the formation of solid Ca_3SiO_5 , which slowed down the further penetration of slag into the refractory.

KEY WORDS: contact angle; wettability; slag; basicity; penetration

1. Introduction

The dolomitic refractory is widely used for containment of steel melts during steelmaking and refining, especially in the production of special steels and clean steels^[1-3], due to its excellent high temperature stability, slag erosion resistance and peeling resistance^[4]. Compared with MgO-C refractory, dolomitic refractory will not cause the increase of carbon in molten steel. Besides, CaO in dolomitic refractory can purify the molten steel by removing inclusions from molten steel^[5-7]. Based on the previous advantages, the dolomitic refractory plays an important role in the production of stainless steels. However, the application of dolomitic refractory is restricted to the hydration of free CaO^[4, 8] at room temperature and the low erosion resistance of low basicity slag^[1]. In MgO-based refractory, MgO was proved to be less reactive during the manufacture of refractory^[5, 6, 9, 10] as well as

during the erosion of refractory. The main erosion focuses on the reaction between slag and CaO^[11].

The consumption of refractory is one of the major costs of steel production. Compared with the hydration of CaO contained refractory, the erosion of refractory is the most important reason for the wear of refractory^[12]. According to Cooper^[13], the erosion of oxides is not only caused by the dissolution or evaporation of the oxides, but also the penetration of liquid phase into the oxides. Penetration of slag into refractory, which is closely related to the wettability between slag and refractory, mainly through pores, grain boundaries and cracks under capillary force.

Ladle Furnace (LF) process is a widely-used secondary steel refining process. During LF process, three electrodes are used to heat the molten steel to the required temperature. By blowing argon gas, adding alloys, and adjusting slag composition, molten steel is deoxidized, desulfurized and alloyed. The erosion of lining refractory not only relates to the chemical reaction, but also some physical processes. The penetration of molten slag into refractory and then the dispersion of refractory grains into slag is one of the damage mechanisms of the refractory. Since the temperature increases during LF process, the wettability between molten slag and refractory varies. Furthermore, the slag basicity also varies during the refining of steel.

Monaghan et al.^[14] investigated the dynamic wetting of slags with different compositions on solid oxides representing inclusion phases (Al_2O_3 , MgAl_2O_4 and $\text{CaO} \cdot \text{Al}_2\text{O}_3$), and concluded that for basic type ladle slags the plateau contact angle was independent of slag composition and for acid type slags the plateau contact angle decreased with increasing basicity. Choi and Lee^[15] conducted a number of experiments with different slag compositions and the results showed that the effect of slag basicity on the wettability depended on the slag composition. The slag basicity might have an opposite effect on the wettability in different composition regions. In the region of low SiO_2 content, the slag with higher CaO content exhibited a smaller contact angle.

The existing researches mainly focused on the wettability between slag and single component substrate representing for inclusion. The interaction between slag and refractory substrate as well as the influence of slag basicity on the penetration were not clearly indicated. In the current study, the wettability between slag and dolomitic ladle lining refractory used for the LF refining of a stainless steel was studied. Experiments were conducted to analyze the effects of slag basicity and holding time on the wettability.

2. Sample preparation

The slag sample was taken during LF refining process in a steel plant. It was the final slag of LF refining process, which was usually considered stable in composition. It was pulverized after cooling down, and became powder containing some iron droplets. The sample was sieved through a 100 mesh sifter to remove iron droplets. After being well mixed, the slag sample was pressed into a cylinder of 0.20 g for each experiment.

The ladle lining refractory brick chosen for the wettability experiment was the one before service, which was completely new. The refractory brick was crushed and ground to small particles, and then the powder was tabletted into thin substrates with 30 mm in diameter and 3 mm in thickness. The substrates were sintered at 1600 °C for 2 h. After sintering, the substrates were polished and the surface roughness of the final substrates were 0.4~0.6 μm .

The chemical composition of slag and refractory determined by XRF are given in **Table 1** and **Table 2** respectively. The refractory mainly consisted of MgO and CaO, while the slag mainly consisted of CaF_2 -CaO- SiO_2 , and both of them contained small amount of other oxides. The basicity of the slag was 2.24. Considering the possible working condition of the refractory^[1, 16], five other slags with basicity of 2.5, 2.0, 1.75, 1.5 and 1.25 as listed in **Table 3** were prepared by adding certain amounts of SiO_2 or CaO.

Table 1 Chemical composition of LF slag

Composition	CaF_2	CaO	SiO_2	MgO	Al_2O_3	CaS	MnO	Fe_2O_3	Cr_2O_3	TiO_2
Content(%)	13.86	54.79	24.51	3.60	1.06	1.23	0.11	0.26	0.24	0.31

Table 2 Chemical composition of ladle lining refractory

Composition	MgO	CaO	SiO_2	Fe_2O_3	Al_2O_3	MnO	S	P_2O_5	Cr_2O_3	TiO_2
Content(%)	56.70	39.80	1.55	1.22	0.52	0.09	0.03	0.04	0.03	0.03

Table 3 Slags with different basicity

Slag	A	B	C	D	E	F
Basicity	2.5	2.24	2.0	1.75	1.5	1.25

3. Experimental setup and procedure

The wettability is usually described by contact angle. In the current study, the sessile drop method^[17] was employed to measure the contact angle between molten slag and dolomitic refractory. The measurement of contact angle was conducted in a horizontal tube furnace. The experimental setup is shown in **Figure 1**. The substrate and the slag sample were placed in the constant temperature zone of the alumina tube. Both sides of the tube were sealed by flange plates equipped with quartz glass. The temperature rose from room temperature to the desired temperature at a heating rate of 5 °C/min. The experiment was conducted in Ar gas (purity 99.999 vol pct), which was purified by Ar purification device and magnesium powder at 600 °C. The light of the lamp passed through the tube and the shadow of samples was recorded by a CCD camera, simultaneously the temperature and time were also recorded. The profile of the liquid drop was extracted by ellipse fitting using a software. The contact angle was obtained by drawing the tangent line of the ellipse at the three-phase contact point. In the current study, eight experiments were conducted to study the effects of slag basicity and holding time on the wettability.

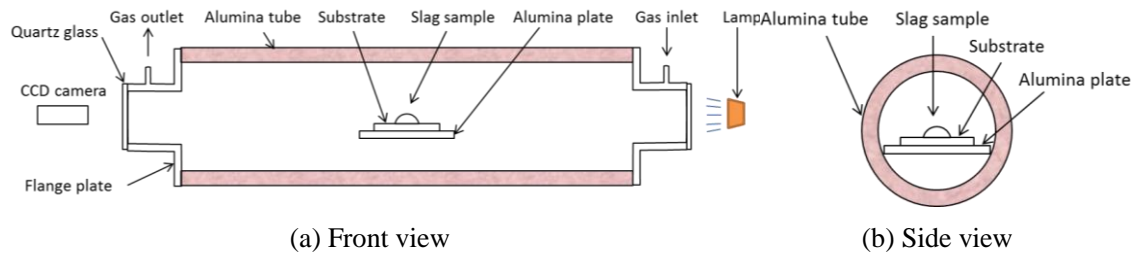


Fig.1 Experimental setup

After the measurement of contact angle, the samples were still protected by Ar gas till the furnace was cooled down to the room temperature. During cooling, the slag was completely pulverized. After removing the powder, the substrate was cut perpendicularly from the center, and the cross section was analyzed by SEM-EDS.

4. Results

4.1 Contact angle between molten slag and dolomitic substrate

The slag usually melts gradually with the rising of temperature in a wide range. The height of the slag decreases with the spreading of slag on the substrate. In the current study, the hemisphere point temperature is considered as the melting point of the slag, and the temperature range corresponding to five-sixths and one-third of the initial height (represented by H) of slag is considered as the melting

temperature range. Both the melting point and melting temperature range are empirical values that have been widely used^[18, 19]. The temperatures measured by this method are shown in **Figure 2**. The slag with higher basicity had higher melting point and wider melting temperature range.

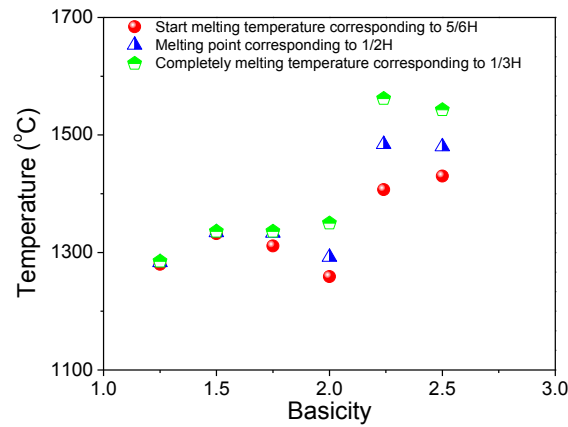


Fig. 2 Melting temperature of slags with different basicity

Once the slag melted and formed an obvious liquid phase at the three-phase point, the contact angle was defined as the initial contact angle in the current study. The initial contact angle was approximately 55°. **Figure 3** shows the contact angle between slags with different basicity and refractory substrates. When the basicity of slag increased from 1.25 to 2.5, the temperature corresponding to the initial contact angle increased. The slag with lower basicity had lower contact angle at the same temperature. The contact angle between the slag with lower basicity and dolomitic substrate decreased fast and finally reached a low value. According to the work done by Monaghan^[14] et al. and Choi^[15] et al., the effect of slag basicity on the contact angle might be quite different for different slag compositions. In the current study, the contact angle between slag with lower basicity and substrate was smaller, which was in consistent with Choi's result. However, the reaction product for all the slags are the same, which will be shown in the following part, the stable contact angle varied little. **Figure 4** shows the contact angle between slags and refractory substrates with different holding time. After 120 minutes, the contact angle reached a stable value of approximately 5°.

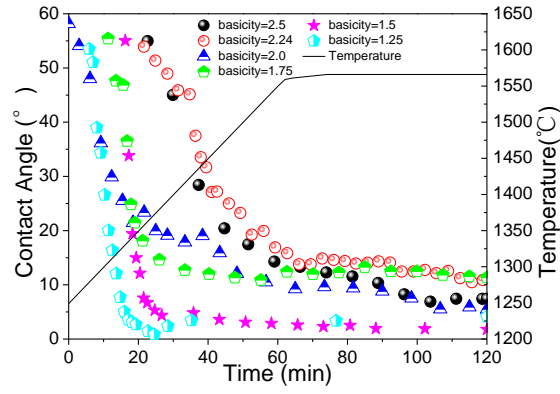


Fig. 3 Contact angle between refractory and slags with different basicity

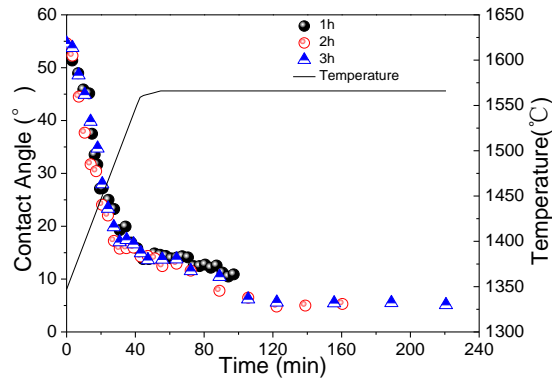


Fig. 4 Contact angle between refractory and slags with different holding times

Figure 5 shows the evolution of slag morphology at different temperatures. The slag with basicity of 2.24 melted in a wide temperature range and spread on the substrate slowly. The contact angle gradually decreased with the spreading of slag. The spreading of slag and the decrease of contact angle in the isothermal stage were much slower compared with those in the temperature rising stage. The other slags show the similar melting process, but in different temperature ranges and at different spreading rates.

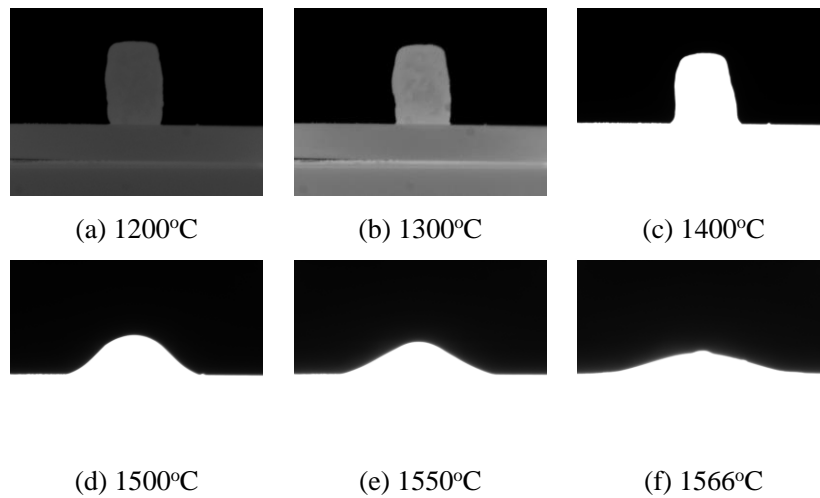


Fig. 5 Morphology of the slag with the basicity of 2.24 at different temperatures

4.2 Penetration of slag into substrate

The cross section of substrates after experiment were analyzed by SEM-EDS. As a reference, another substrate without involving in the wetting experiment was prepared in the same way. **Figure 6** shows the SEM images of the two substrates. The original substrate mainly consisted of several big grains ($<150\text{ }\mu\text{m}$), large amount of small grains ($\sim 7\text{ }\mu\text{m}$) and the continuous phase among grains. Some pores distributed along the margin of big grains. The EDS result confirmed that both big grains and small grains were MgO , and the continuous phase was CaO . Small amount of impurities mainly existed in the CaO phase. The substrate after experiment showed similar structure. However, part of CaO was replaced by the penetrated slag phase. **Figure 7** shows the composition distribution of the substrate. Since the slag was pulverized during cooling, only a thin slag layer stuck on the substrate. The composition of the slag layer above the substrate detected by EDS indicated little difference with the penetrated slag in the substrate. The typical composition of different locations presented with different color is listed in **Table 4**. Considering the inaccuracy of EDS for the element fluorine, the detected CaF_2 content might be lower than the true value, leading to a higher content of CaO , especially for the light grey area in **Table 4**. The slag penetrated into the substrate through grain boundaries, micro-cracks and pores. All the other substrates showed similar structures and compositions.

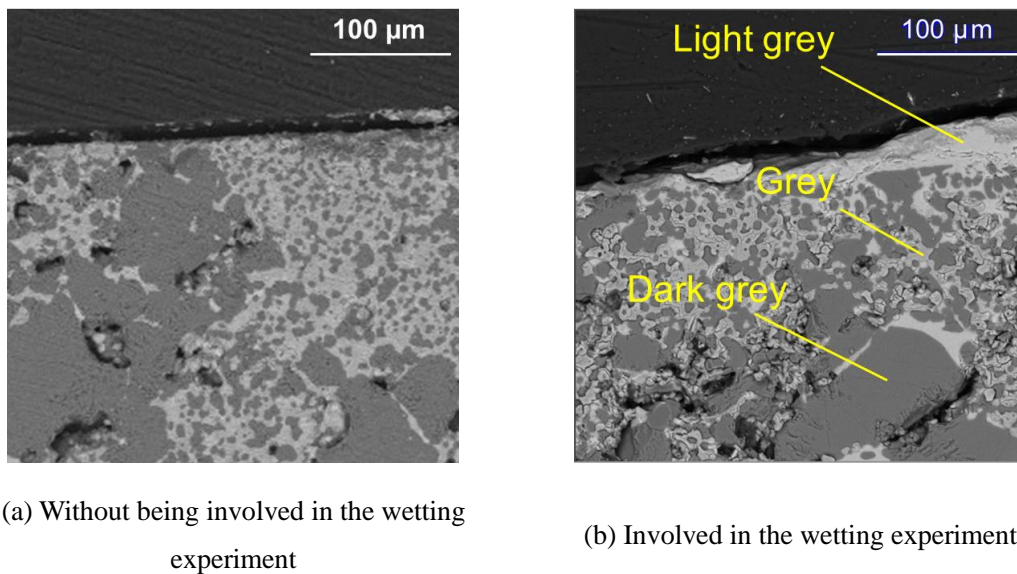


Fig. 6 SEM image of the substrate

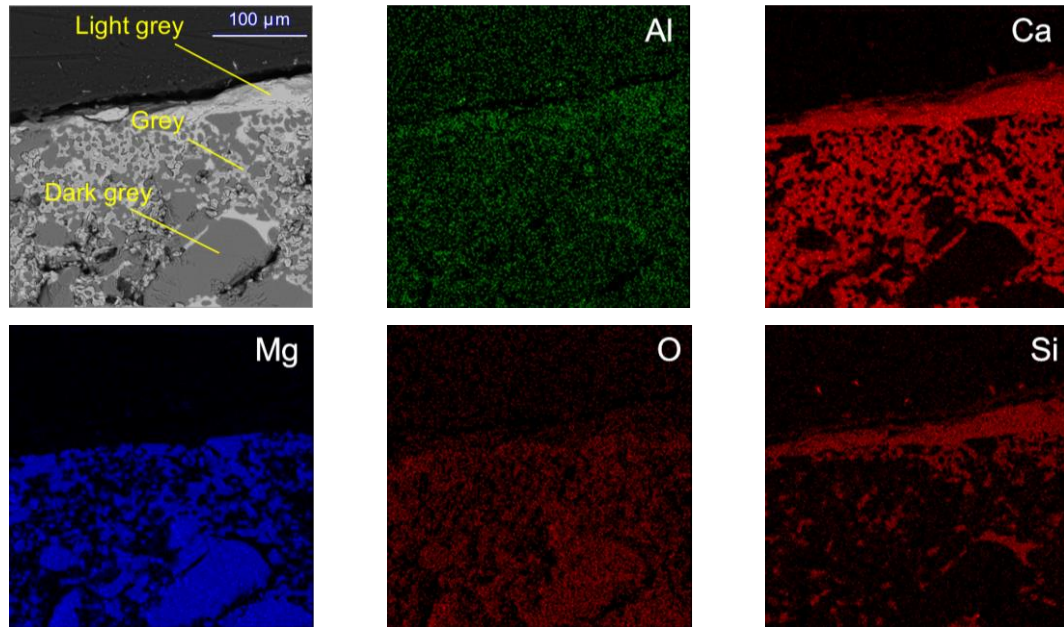


Fig. 7 Composition mapping of the cross section of one substrate

Table 4 EDS composition at different locations

Slag basicity		CaO	SiO ₂	Al ₂ O ₃	MgO	Fe ₂ O ₃	CaF ₂	TiO ₂	MnO	Cr ₂ O ₃
2.24	Light Grey	82.78	15.34	0.27	0.47	0	0.44	0.12	0.37	0.21
	Grey	96.47	0.32	0.14	1.74	0.53	0.15	0.25	0.29	0.11
	Dark grey	2.17	0.16	1.13	91.96	1.82	0.77	0	0.58	1.42

Since the penetration of slag into refractory substrate was hardly uniform along the interface, no remarkable penetration layer could be observed, the line scanning perpendicular to the surface of the substrate could hardly accurately illustrate the penetration depth of the slag. In the current study, several equally spaced locations at the interface between slag and substrate were chosen to perform EDS composition mapping. The scanning started from the interface to the inner of the substrate, as shown in **Figure 8**. Then, the result of the EDS mapping was converted to intensity data according to the gray value of scanning point. The distribution of elements were finally represented in the form of oxide, which is shown in **Figure 9**. It indicated that the magnesia did not dissolve into the slag, and the distribution of silica and magnesia could be used to represent the slag and substrate respectively. The outline of the magnesia characterized by red line in **Figure 9(c)** represented the interface between the slag and the substrate. Thus, the distribution of silica in **Figure 9(a)** was separated into two parts, only the silica below the interfacial line was the penetrated slag, shown in **Figure 9(c)**, and that above the interfacial line was the slag stuck on the surface.

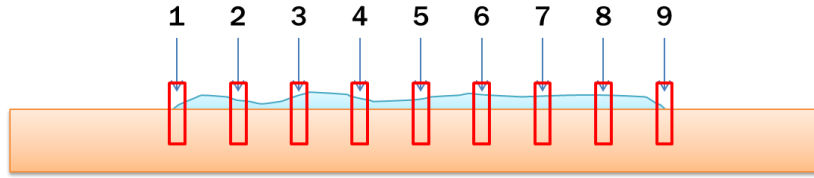


Fig. 8 Schematic of the scanning area

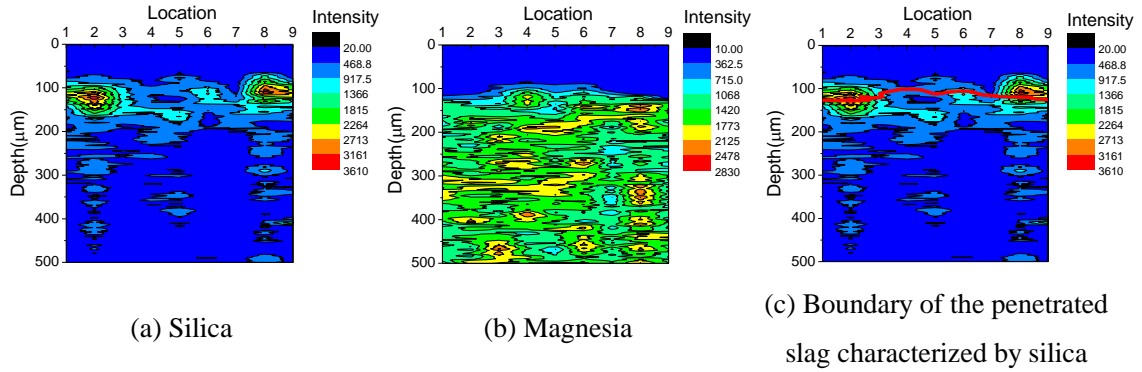
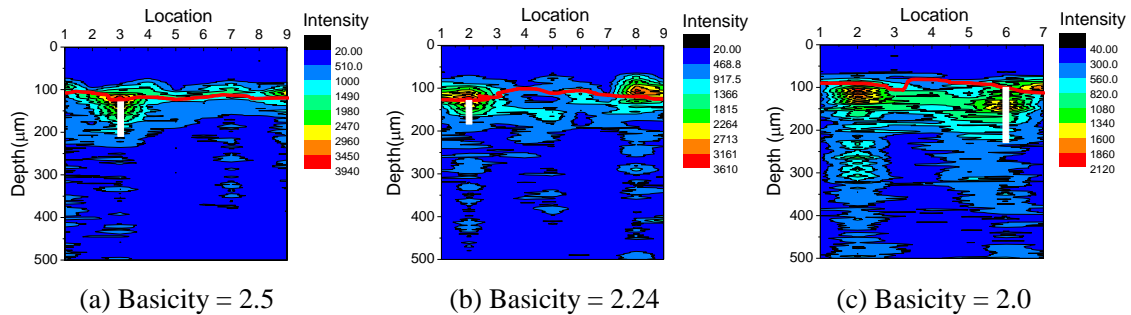


Fig. 9 Distribution of silica and magnesia

Figure 10 and **Figure 11** show the distribution of silica in the substrate after experiment. Slag F spread out of the margin of the substrate in a short time, so that only small amount of slag left on the substrate, and no obvious penetration was observed. Both of the substrates contacted with slag D and E cracked during cooling, mainly caused by the penetration of slag and the different expansion coefficients of the three phases listed in **Table 4**. The substrate contacting with slag D was seriously broken that no such intact cross section of the substrate could be prepared to show the element distribution. In all experiments, the silica-rich area didn't locate at the center where the slag contacted with the substrate during all the experiment time. Instead, the silica concentrated in one ring between the center and the margin of the contact area. **Figure 12** illustrates the schematic penetration phenomenon.



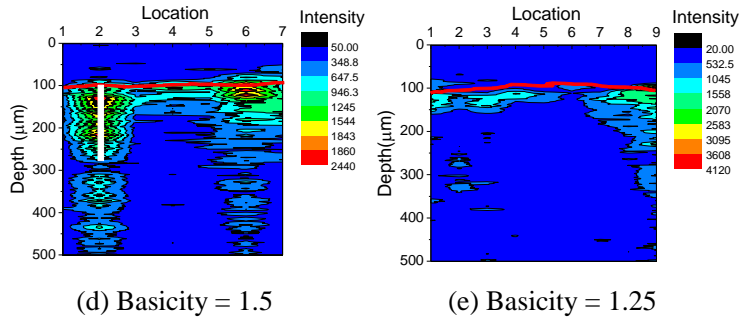


Fig. 10 Penetration of slag with different basicity into refractory characterized by silica

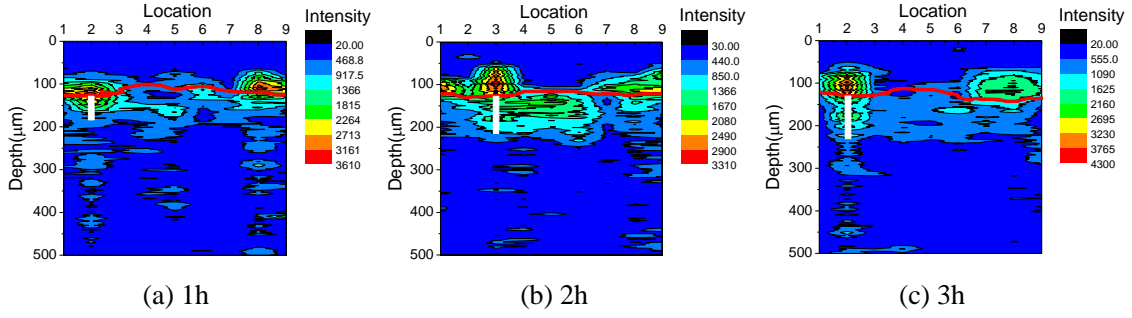


Fig. 11 Penetration of slag into substrate with different holding times characterized by silica


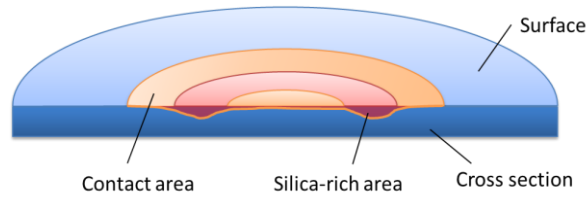


Fig. 12 Schematic of the penetration area

5. Interaction between slag and substrate

After the measurement of contact angle, the surface of the substrate and the pulverized slag together with the original sample were detected by XRD and the results are shown in **Figure 13**.

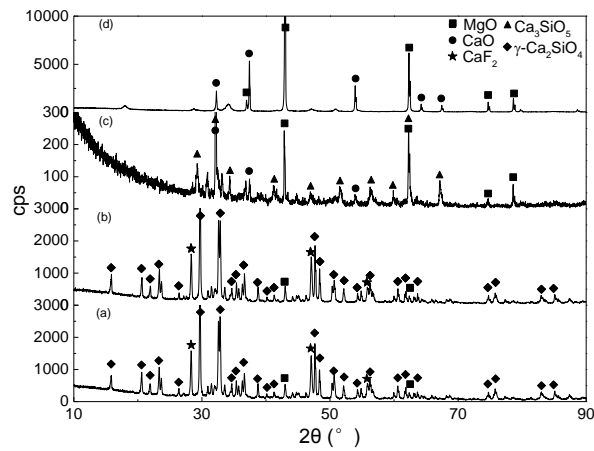

(a) slag before experiment (b) slag after experiment
(c) substrate after experiment (d) substrate before experiment

Fig. 13 XRD result of substrates and slags

There were no big differences between the pulverized slag and the original slag. The main composition in the slag was $\gamma\text{-Ca}_2\text{SiO}_4$. The phase transformation of Ca_2SiO_4 during cooling was the main reason for the pulverization of slag^[20]. Compared with the original substrate, the composition of slag stuck on the substrate was quite different from that of the pulverized slag. Except for MgO and CaO, Ca_3SiO_5 phase which was formed above 1250 °C was generated in the substrate during the experiment according to **Equation 1**. The chemical reaction mainly occurred at the interface. CaO in the dolomitic substrate provided the source for the formation of Ca_3SiO_5 , meanwhile, MgO promoted the formation of Ca_3SiO_5 ^[21].



The mass of slag in each experiment was 0.2 g. Taking the main compositions in the slag, i.e. $\text{CaF}_2\text{-CaO-SiO}_2\text{-MgO-Al}_2\text{O}_3$, into consideration, the equilibrium phases are calculated by Factsage 7.0. Most of CaO is transformed to complex compounds or dissolved into liquid slag, while part of MgO in the slag is kept unreacted, as shown in **Figure 14**. When the slag contacts with the dolomitic substrate, CaO and MgO in the substrate may react with or dissolve into the liquid slag. Assume that 2.0 g slag reacts with 5.0 g dolomitic, and the dolomitic substrate only contains MgO and CaO. The ration of CaO and MgO in dolomitic substrate participating in the reaction between slag and substrate are shown in **Figure 15**. MgO in the substrate is inert under the experiment condition. only CaO in the substrate can react with or dissolve into the slag, which means that the spreading and penetration of slag are not only a physical process but also a chemical process. Except for the traditional channels, such as grain boundaries, micro cracks and pores, the liquid slag may penetrate into the substrate through the channel where CaO exists once CaO dissolves into the liquid slag.



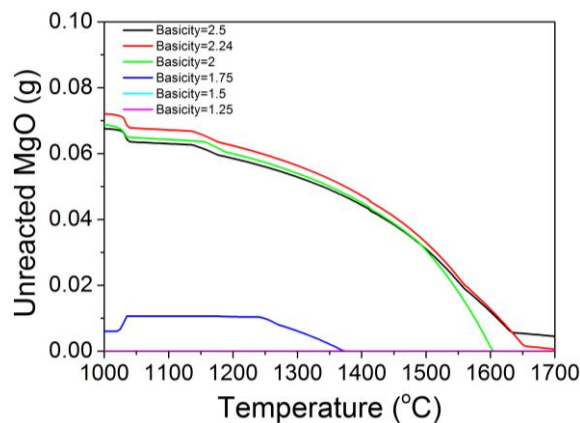


Fig. 14 Unreacted MgO in the slag

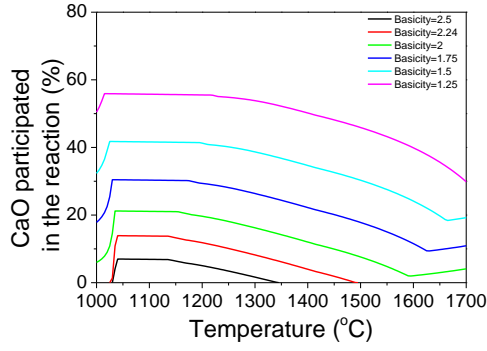

(a) CaO

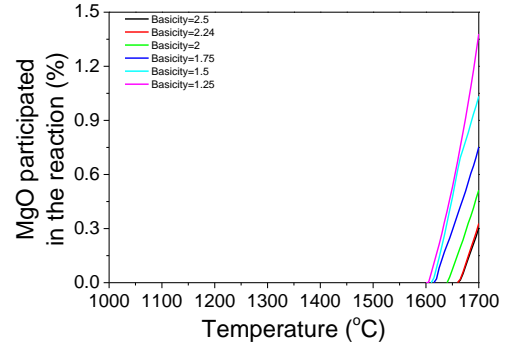

(b) MgO

Fig. 15 CaO and MgO in the substrate participating in the reaction between slag and substrate

6. Factors affecting the penetration depth

6.1 Slag basicity

As is mentioned above, there were large grains, irregular pores and micro-cracks in the substrate, providing channels for the penetration of slag. The slag penetrated into the substrate much deeper at the location with more pores. However, the distribution of pores was hardly uniform. As a result, the largest penetration depth was random and the amount of the penetrated slag was small at the deepest penetrated location. In the current study, considering the SEM images and the scanning intensity, the largest penetration depth of the slag was only focused on the silica-rich area, not including the trace content at deeper area. The red line shown in **Figure 10** and **Figure 11** indicates the interface between slag and substrate, and is defined as the zero penetration depth. The largest penetration depth in the two figures are marked by bold white line. The largest penetration depth of the four substrates are shown in **Figure 16**, indicating the relationship between slag basicity and penetration depth. The slag with lower basicity had larger penetration depth. Similar results were reported by Luz^[22]. In the current study, the largest penetration depth was 178 μm for the slag with basicity of 1.5.

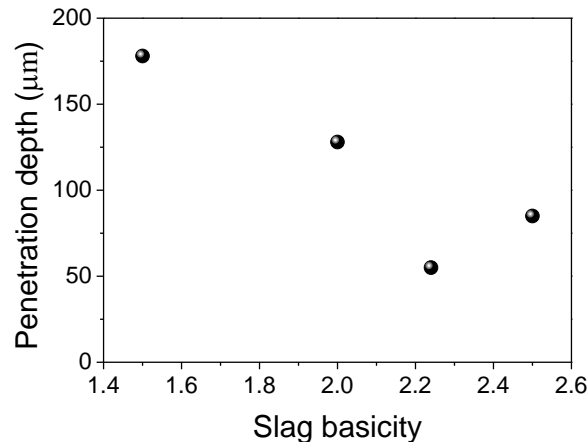


Fig. 16 Penetration depth of the slag with different basicity

The slag penetrated into substrate mainly through grain boundaries, micro cracks and pores. The capillary force was the driven force for the penetration of slag. The wettability between molten slag and substrate was one of the important factors that affecting the capillary force. Slag with lower basicity wet the substrate more easily (**Figure 3**). Therefore, a larger penetration depth could be obtained.

CaO coming from the substrate might dissolve into the liquid slag, providing the channel for the penetration of slag. The capacity for the dissolution of CaO depended on the CaO saturability of the slag. **Figure 17** shows the saturated CaO content in all liquid slags. There were no big differences between the different slags. Since the slag with higher basicity contained more CaO, fewer would come from the substrate. On the contrary, for the slag with lower basicity, more CaO coming from the substrate would dissolve into the liquid slag, providing extra penetration channel and causing the increase of penetration depth. By the way, the increase of temperature accelerated the dissolution of CaO from substrate.

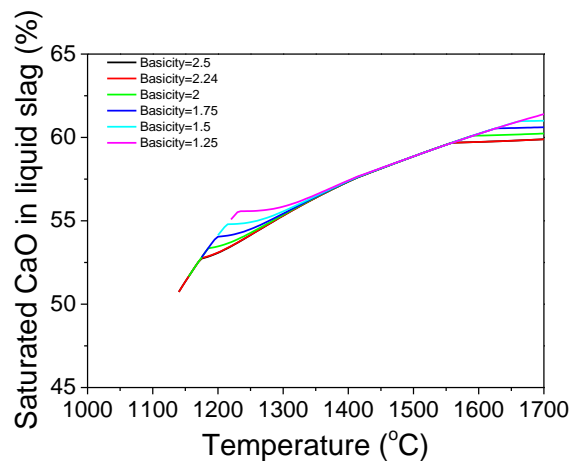


Fig. 17 Variation of saturated CaO in liquid slag

6.2 Contact time

Figure 18 shows the relationship between holding time and penetration depth. With the increase of holding time, the penetration depth increased. Heo^[23] et al. studied the reactive wetting phenomena of MgO-C refractories in contact with CaO-SiO₂ slag and concluded that an intrinsic contact angle existed during initial 4s without chemical reaction. Park^[24] et al. also indicated that during the initial short period, the dissolution of oxide into slag was neglected. In the current study, when the newly contact area was covered by the slag, the initial penetration was caused by the flow of slag through grain boundaries, micro cracks and pores without any reaction. The initial penetration finished in a short time, within which the dissolution of the solid oxide into the slag was relatively slow^[25]. The following penetration was accompanied with the dissolution of CaO until the slag was saturated with CaO. Once the Ca₃SiO₅ was generated, the solid phase under the experiment temperature would prevent the flow of the original slag. The further penetration of slag was caused by diffusion. **Equation 2** shows ideal penetration depth for an unreactive system. Both the penetration of slag according to **Equation 2** or the diffusion of slag were closely related to the time, the increase of time lead to the deeper penetration. Pretending that other parameters are replaced by a penetration rate k , as shown in **Equation 3**. The penetration rate k is approximately 58 $\mu\text{m}/\text{h}^{0.5}$ according to **Figure 18**. Meanwhile, the CaO also diffused to the slag phase. In **Figure 12**, the silica-rich area provided a relative big interfacial area between the penetrated slag and the dolomitic substrate for the diffusion of CaO. As a result, the silica-rich area in the substrate was also the area of slag saturated with CaO above the substrate.

$$X = \sqrt{\frac{r\gamma \cos \theta}{2\eta}} t \quad (2)$$

$$X = k\sqrt{t} \quad (3)$$

where X is the penetration depth, r is the radius of the capillary channel, γ is the surface tension of the liquid phase, θ is the contact angle, η is the viscosity and t is the penetration time.

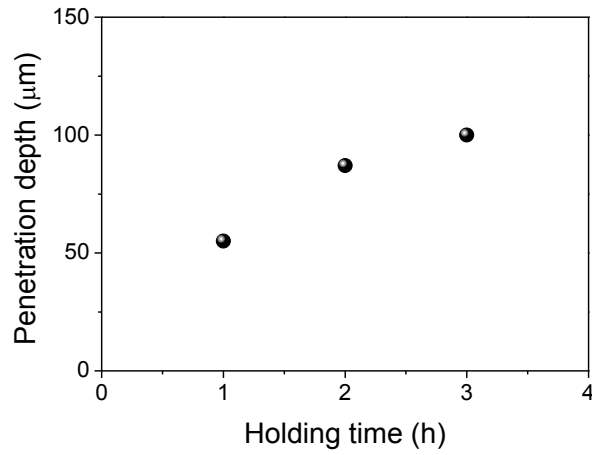


Fig. 18 Penetration depth of the slag with different holding times

Although the contact time between slag and substrate in the center was longer than that in the margin, the initial contact in the center caused the primary formation of Ca_3SiO_5 , even before the melting of slag. Thus the shallow penetration depth in the center was observed.

7. Conclusions

(1) In the current study, the contact angle continuously decreased with the increase of temperature. The stable contact angle between the substrate and the slag saturated with CaO at 1566 °C was approximately 5°.

(2) MgO in the dolomitic substrate did not react with or dissolve into slag for all slags in the current study. The CaO in the dolomitic substrate might react with or dissolve into liquid slag. The substrate could provide extra penetration channel once the CaO dissolved into liquid slag, accelerating the penetration of slag. The CaO in the substrate also reacted with slag and formed Ca_3SiO_5 , preventing the penetration of slag.

(3) Slag with lower basicity started to wet the substrate at lower temperature, and the contact angle decreased fast in a narrow temperature range in the temperature rising stage. The final stable contact angle showed no big differences between all slags, i.e. approximately 5°. The strong reactive wetting between slag with lower basicity and dolomitic refractory was one of the reason for the fast decrease of the contact angle.

(4) Slag with lower basicity had bigger capacity for the dissolution of CaO, thus achieved larger penetration depth in the substrate. The largest penetration depth was 178 μm for the slag with basicity of 1.5.

(5) With the increase of holding time from 1 h to 3 h, the contact angle between slag and substrate decreased from 10.5° to 5.0°, and the penetration depth of slag increased from 55 μm to 100 μm.

Acknowledgements

The authors are grateful for support from the National Science Foundation China (Grant No. 51274034, No. 51334002, No.51404019 and No.51504020), Beijing Key Laboratory of Green Recycling and Extraction of Metals (GREM), the Laboratory of Green Process Metallurgy and Modeling (GPM²) and the High Quality Steel Consortium (HQSC) at the School of Metallurgical and Ecological Engineering at University of Science and Technology Beijing (USTB), China. Correspondence author: Lifeng Zhang, E-mail:zhanglifeng@ustb.edu.cn

References

- [1] Y. Liang, Y. Li. Slag resistance of MgO-CaO bricks[J]. *Refractories*, 2009, 43(4): 263-266.
- [2] X. Zhong. Looking ahead-A new generation of high performance refractory ceramics[J]. *China's Refractories*, 2002, 11(3): 3-13.
- [3] W. Dai, J. Yu. Refractory for clean steel making[J]. *Journal of Materials and Metallurgy*, 2003, 2(1): 3-9.
- [4] Z. Li, S. Zhang, W. E. Lee. Improving the hydration resistance of lime-based refractory materials[J]. *International Materials Reviews*, 2008, 53(1): 1-20.
- [5] H. Zhang, H. Zhao, J. Chen, et al. Defect study of MgO-CaO material doped with CeO₂[J]. *Advances in Materials Science and Engineering*, 2013, 10(4): 1-5.
- [6] M. Chen, C. Lu, J. Yu. Improvement in performance of MgO-CaO refractories by addition of nano-sized ZrO₂[J]. *Journal of the European Ceramic Society*, 2007, 27(16): 4633-4638.
- [7] B. Huang, W. Zhang, H. Gu, et al. Resistance of MgO-CaO unburned brick to refining slag[J]. *Journal of Iron and Steel Research*, 2004, 16(1): 10-14.
- [8] F. Kashaninia, H. Sarpoolaky, A. R. Bagheri, et al. Improving hydration resistance of magnesia-doloma refractories by iron oxide addition[J]. *Iranian Journal of Materials Science and Engineering*, 2011, 8(4): 34-40.
- [9] A. G. T. Martinez, M. A. Camerucci, A. L. Cavalieri, et al. Sintering behavior of periclase-doloma refractory mixes[J]. *Journal of the European Ceramic Society*, 2009, 29(4): 581-586.
- [10] G. Qiu, C. Yue, X. Li, et al. Preparation and characterization of regenerated MgO-CaO refractory bricks sintered under different atmospheres[J]. *International Journal of Minerals Metallurgy and Materials*, 2014, 21(12): 1233-1240.
- [11] X. L. Coq, B. Dupré, C. Gleitzer, et al. Slag corrosion of dolomite-carbon refractories[J]. *Steel Research*, 1990, 61(12): 593-597.
- [12] D. N. Boccaccini, M. Cannio, M. Romagnoli, et al. The pO-index and R ratio gap methods for the assessment of corrosion risk in refractory materials in contact with glass melts[J]. *Journal of the American Ceramic Society*, 2010, 93(5): 1355-1363.
- [13] A. R. Cooper. Kinetics of refractory corrosion, in *Proceedings of the educational symposium on refractories in sagging environments: Ceramic engineering and science proceedings 1981*, John Wiley & Sons, Inc. 1063-1089.

- [14] B. J. Monaghan, H. Abdeyazdan, N. Dogan, et al. Effect of slag composition on wettability of oxide inclusions[J]. ISIJ International, 2015, 55(9): 1834-1840.
- [15] J. Y. Choi, H. G. Lee. Wetting of solid Al_2O_3 with molten $\text{CaO-Al}_2\text{O}_3\text{-SiO}_2$ [J]. ISIJ International, 2003, 43(9): 1348-1355.
- [16] S. Li, Z. Jiang, Z. Huang, et al. Effect of refining slag basicity on inclusions in 304 stainless steel[J]. Iron and Steel, 2010, 45(12): 26-29.
- [17] N. Eustathopoulos, M. G. Nicholas, B. Drevet. Wettability at high temperatures[M]. Pergamon, 1999.
- [18] X. Liang, Y. Jin, Y. Wang. Effect of additives on melting point and viscosity of RH refining slag[J]. Open Materials Science Journal, 2011, 5(1): 9-14.
- [19] H. Wang, G. Li, B. Li, et al. Effect of B_2O_3 on melting temperature of CaO -based ladle refining slag[J]. Journal of Iron & Steel Research International, 2010, 17(10): 18-22.
- [20] R. T. d. Cruz, S. R. Bragança. Evaluation of the protective C_2S layer in the corrosion process of doloma-C refractories[J]. Ceramics International, 2015, 41(3, Part B): 4775-4781.
- [21] X. Liu, Y. Li, N. Zhang. Influence of MgO on the formation of Ca_3SiO_5 and $3\text{CaO}\cdot 3\text{Al}_2\text{O}_3\cdot \text{CaSO}_4$ minerals in alite-sulphoaluminate cement[J]. Cement & Concrete Research, 2002, 32(7): 1125-1129.
- [22] A. P. Luz, F. C. Leite, M. A. M. Brito, et al. Slag conditioning effects on MgO-C refractory corrosion performance[J]. Ceramics International, 2013, 39(7): 7507-7515.
- [23] S. H. Heo, K. Lee, Y. Chung. Reactive wetting phenomena of MgO-C refractories in contact with CaO-SiO_2 slag[J]. Transactions of Nonferrous Metals Society of China, 2012, 22(35): 870-875.
- [24] J. Park, K. Lee, J. J. Pak, et al. Initial wetting and spreading phenomena of a CaO-SiO_2 liquid slag on MgO substrates[J]. Transactions of the Iron and Steel Institute of Japan, 2014, 54(9): 2059-2063.
- [25] Y. V. Sveshkov, V. A. Kalmykov, V. G. Borisov, et al. Wetting of refractories of the CaO-MgO system by slags[J]. Refractories, 1978, 19(9-10): 655-659.